

THE EFFECT OF ANNEALING ON MECHANICAL PROPERTIES OF AUTOMOTIVE STEEL SHEETS

Received – Priljeno: 2019-11-21

Accepted – Prihvaćeno: 2020-02-15

Preliminary Note – Prethodno priopćenje

This paper deals with mechanical properties of galvanized automotive steel sheet. The composition of the zinc coating modifies as a result of the annealing after galvanizing, thereby its local mechanical properties change. Presented research is therefore aimed at determination the change in tensile properties of steel due to annealing, which is an important part of galvanizing technology. Annealing of galvanized steel samples was carried out at 500 °C with different holding times at annealing temperature. Changes in both tensile strength and normal anisotropy coefficient, a decrease of yield strength and an increase of ductility were found for examined steel.

Keywords: IF steel, sheet, galvanize, annealing, mechanical properties.

INTRODUCTION

Steel is a traditional material used in the production of sheets [1] for the automotive industry which is currently the most dynamically developing industry. Its rapid development is largely facilitated by continuous improvement of functional properties and quality of automobiles. This work is focused on the tension properties of galvanized steel intended to be used in automobiles – a deep-drawing IF (Interstitial Free) steel. The effect of annealing on the tensile properties of galvanized IF steel was determined.

One of the metal coatings used to protect steel, is the zinc coating [2]. Zinc coatings belong to the best known and the longest applied methods of protection of metal products against corrosion. The reason why zinc is used is its ability of excellent anticorrosive protection with regard to the double effect of the coating: (i) the barrier effect and (ii) the cathodic protection. Galvanizing steel by dipping it into molten zinc is the most important and most frequently used method of surface protection [3]. This technology is used in continuous processes, such as hot-dip galvanizing of straps and wires, in semiautomatic lines for hot-dip galvanizing of pipes, as well as hot-dip galvanizing of various types of steel parts and structures in the process of piece galvanizing. The automotive industry is a significant consumer of galvanized steel sheets. At present, a major part of galvanized steel sheets is manufactured by hot-dip galvanizing in continuous lines using the technology referred to as the Sendzimir process.

Hot-dip galvanizing is a metallurgical process in which a coating is formed on the steel surface as a result

of the reaction between the base material and molten zinc in a bath. The result thereof is a multi-phase composition of the zinc coating [4]. The reaction between pure-metal steel surface and molten zinc produces, in an order corresponding to the phase equilibrium diagram of Fe – Zn [5]. In a continuous process, it is possible to suppress the formation of several layers by adding Al into the bath in the amount of 0,15 – 0,30 % [6]; this brings overall improvement in the adhesion of the Zn coating due to the formation of a Fe_2Al_3 semi-layer [4] which prevents the reaction between Fe and Al. The addition of 0,2 to 0,3 % Al results in the formation of the layer of pure Zn. Only after the Fe_2Al_3 interim layer is dissolved, normal formation of intermetallic phases begins, even faster than without aluminium [5].

Galvanized coatings [4] are formed by galvanizing which may be preceded by hot-dip galvanizing, electrolytic galvanizing, or vapour galvanizing, most frequently within the temperature range of 440 – 550 °C. The galvanizing after galvanizing is the process that results in the transformation of pure Zn inside the coating into intermetallic phases Fe – Zn through diffusion between Zn and the steel base.

EXPERIMENTAL Steel

For experiments was used deep-drawing IF steel with ferrite microstructure, chemical composition is presented in Table 1. Mechanical properties (0,2 % offset yield strength $R_{p0,2}$, tensile strength R_m , elongation A_{80} , normal anisotropy coefficient r and strain hardening exponent n) are shown in Table 2.

IF steels are used for production extra deep drawing hot-dip galvanized sheets for demanding automotive stampings [7]. With respect to the desired properties of conditional development of adequate texture and more

L. Ambriško, e-mail: ludovit.ambriško@tuke.sk, D. Marasová, J. Šaderová, P. Maras - Technical University of Košice, Faculty of Mining, Ecology, Process Control and Geotechnologies, Košice, Slovakia

Table 1 **Chemical composition of IF steel**

| Chemical composition / wt. % | | | | |
|------------------------------|-------|--------|-------|-------|
| C | Mn | Al | P | S |
| 0,005 | 0,298 | 0,0439 | 0,059 | 0,008 |
| Si | Ti | Nb | Cu | Cr |
| 0,008 | 0,034 | 0,039 | 0,021 | 0,012 |
| Ni | As | N | V | Zr |
| 0,009 | 0,006 | 0,003 | 0,001 | 0,001 |
| Sn | Sb | Mo | B | |
| 0,003 | 0,002 | 0,002 | 0,001 | |

Table 2 **Mechanical properties of IF steel**

| Steel | $R_{p0,2}$ / MPa | R_m / MPa | A_{80} / % | r | n |
|-------|---------------------|----------------|-----------------|------|------|
| IF | 281 | 386 | 32,8 | 1,95 | 0,19 |

stringent requirements concerning, for example aging, it is necessary to attach the greatest extent possible and as low concentrations of dissolved interstitial compounds to stable carbide formers and nitride formers [8]. IF steels have interstitial C and N atoms untied to stable forms, and that don't require additional overage and may be processed at a high heating rate and movement of the band and which are necessary for galvanizing or continuously annealing [9]. IF steels were developed to achieve extremely high deep drawing levels. This property is preferred at the expense of strength values, which normally degrades the ability of deep drawing [10–12].

In terms of physical metallurgy, the nature of IF steels is simple. It is a structure of very pure ferrite, which properties are controlled mainly by grain size. Difficulties arise in choosing practical measures that lead to their optimum size, conditional upon the desired anisotropy of properties. Microalloying elements Ti, Nb, or their combinations play an important role not only in binding free interstitials improving ductility and resistance to deformation aging, but also in the kinetics of recrystallization. It should be pointed out, that the appropriate choice of their contents is not unambiguous and is always dependent on the possible thermal conditions of hot rolling, or on annealing parameters of cold rolled strips [7].

Thermodynamic conditions of hot rolling of IF steels, in particular the entrance heating temperature of slabs, the rolling temperature, the strip cooling rate from the rolling temperatures should be chosen with regard to the knowledge of the recrystallization kinetics and particle precipitation processes. The precipitate is already present after hot rolling in all types of IF steels. The dispersion of precipitates and the carbon state play a very important role in recrystallization inhibiting [8].

Achieving the potential of the deep-drawing properties offered by IF steels is possible directly by galvanizing on continuous lines, providing controlled hot rolling that allows controlled precipitation of TiCN in both size and particle number. The hot rolling is carried out at temperatures above 900 °C in the austenitic region where the TiCN particles are completely dissolved.

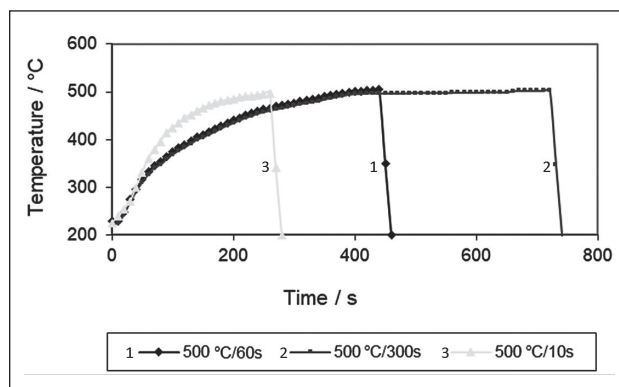


Figure 1 Annealing of IF steel

Their precipitation is effected by subsequent cooling and curling. Curling temperatures should be relatively high, but with respect to belt morbidity, they are maintained at 650 to 690 °C. The cold rolling is done by removing 70 to 80 %, after which the texture of type (111) has been favorably developed [10].

IF steels have a very low yield point, below 160 MPa, and are fully ageless due to the absence of interstitial reinforcement. The steels have a high ductility above 42 %, a mean normal anisotropy coefficient r above 1,7 and also a high strain hardening exponent n [10].

Annealing

Samples were annealed at 500 °C in a furnace type 7/5 KPO with forced circulation by contact heating on the refractory brick, followed by cooling in air, for 3 different times: 10, 60, and 300 s (Figure 1). Longer annealing times were chosen because of the higher phosphorus content in the steel, which affects the composition of the galvanneal coating [12].

RESULTS AND DISCUSSION

The Figure 2 describes the uniaxial tensile testing the IF steel in all states, aimed to identify the strain characteristics corresponding to the given stresses. There are obviously different mechanical properties. Obtained values after annealing are listed in Table 3.

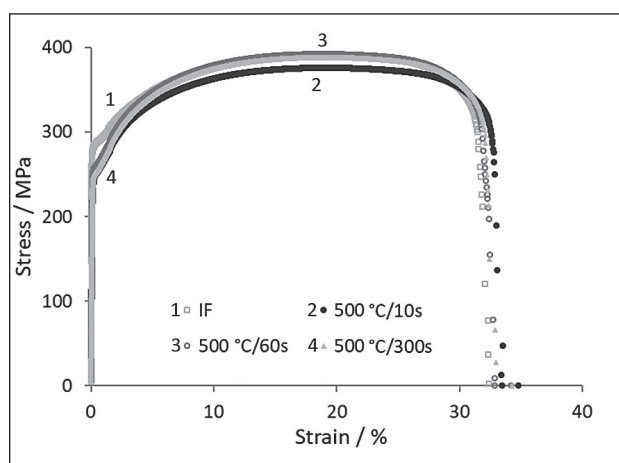


Figure 2 Stress-strain diagram of examined steel, IF - designation for unannealed state

Table 3 Mechanical properties of annealed steel

| Annealing | $R_{p0,2}$ / MPa | R_m / MPa | A_{80} / % | r | n |
|---------------|------------------|-------------|--------------|-----|------|
| 500 °C/10 s | 249 | 376 | 33,5 | 2,1 | 0,19 |
| 500 °C/60 s | 257 | 392 | 33 | 2 | 0,19 |
| 500 °C/ 300 s | 251 | 387 | 33,2 | 1,9 | 0,19 |

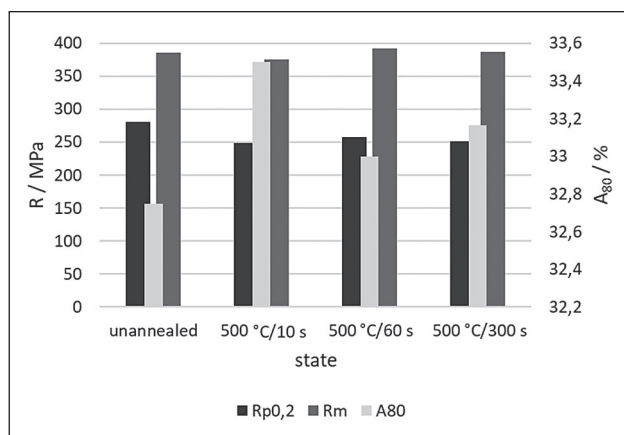


Figure 3 Histogram of obtained mechanical properties - yield strength $R_{p0,2}$, tensile strength R_m , elongation A_{80}

The mechanical properties of the examined steel after annealing differ. Measured yield strength $R_{p0,2}$, tensile strength R_m , elongation A_{80} and normal anisotropy coefficient r are different. Strain hardening exponent n hasn't changed after any annealing.

Yield strength of annealed samples of IF steel is lower by 8,5 – 11,4 % than in the initial state. Tensile strength after annealing lasting 10 s is decreased by 2,6 %, it increased by 0,3 – 1,6 % for the other annealing (both 500 °C/60 s and 500 °C/300 s). The maximum value was found on annealing 500 °C/60 s. Elongation of the annealed samples of the investigated steel is higher by 0,6 – 2,1 % than for unannealed steel. The maximum elongation occurred at annealing 500 °C/10 s. Normal anisotropy coefficient of annealed states differ from default state in the range -2,6 – 7,7 %. Figure 3 documents the comparison of determined mechanical properties.

CONCLUSION

The galvannealing technology [13], consisting in annealing of galvanized steel sheets, was applied to the specimens of deep-drawing hot-dip galvanized IF steel sheet. Galvannealing modified the composition of the zinc coating which after the annealing consisted of intermetallic phases Zn – Fe. As a result, its mechanical properties change. The results of the experiments con-

firmed the change of both tensile strength and normal anisotropy coefficient, a decrease of yield strength and an increase of ductility of annealed samples of IF steel.

Acknowledgements

This work was supported by the project VEGA 1/0429/18.

REFERENCES

- [1] D. Malindžák, J. Šaderová, D. Vitko, M. Malindžáková, A. Gazda, The methodology and model for in-process inventories calculation in the conditions of metallurgy production, *Metalurgija* 54 (2015) 1, 227-230.
- [2] J. Brezinová, Temporary protection of zinc coating applied by blasting technology, *Koroze a ochrana materiálu* 3 (2005), 50-54 (in Slovak).
- [3] M. Mohyla, Technology of metal surface treatment, VSB TU, Ostrava 1995 (in Czech).
- [4] F. Šimčák, J. Billy, Sheets for the automotive industry and their surface finishes, *Zváranie – Svařování* 9-10 (2003), 190-191 (in Slovak).
- [5] V. Kraus, Surfaces and their treatment, ZU, Plzeň 2000 (in Czech).
- [6] M. Longauerová, J. Grutková, S. Longauer, V. Frič, Structure and microhardness of Zn coatings, *Materiál v inžinierskej praxi*, TUKE, Herľany, 1998, 253-258 (in Slovak).
- [7] J. Billy, P. Slávik, L. Mikolaj, K. Hala, J. Záboj, Hot-dip galvanized sheets produced by VSŽ for the automotive industry, *Plechý pre automobilový priemysel*, VSŽ, Stará Lesná 1997, 25-31 (in Slovak).
- [8] H.K.D.H. Bhadeshia, R.W.K. Honeycombe, *Steels: microstructure and properties*, Elsevier, Oxford 2006.
- [9] L. Ambriško, M. Cehlár, D. Marasová, The rate of stable crack growth (SCG) in automotive steels sheets, *Metalurgija* 56 (2017) 3-4, 396-398.
- [10] J. Billy, B. Štefan, P. Slávik, V. Gašpar, L. Mikolaj, J. Záboj, Specifics of hot-dip galvanized sheets for the purposes of bodywork, *Hutnícke listy* 5 (1994), 15-20 (in Slovak).
- [11] L. Ambriško, L. Pešek, Determination the crack growth resistance of automotive steel sheets, *Chemické listy* 105 (2011), 767-768.
- [12] I. Shpakov, A. Mironenko, Non-destructive inspection of steel wire ropes, *Transport & Logistics: the International Journal* 15 (2015) 37, 1-6.
- [13] R. Gouel, H. James, *On – line measurement of galvanneal coatings*, GALVATECH '95 – The Use and Manufacture of Zinc and Zinc Alloy Coated Sheet Steel Products into the 21st Century, Chicago 1995, 88-95.

Note: The English Language translation was done by Miriam Valčáková, Košice, Slovakia.