

Sezgin Koray Gülsoy¹, Ülkü Burcu Gitti¹, Ayhan Gençer¹

Comparison of Soda, Kraft, and DES Pulp Properties of European Black Poplar

Usporedba svojstava natronske, kraft i DES celuloze od drva europske crne topole

ORIGINAL SCIENTIFIC PAPER

Izvorni znanstveni rad

Received – prispjelo: 28. 3. 2021.

Accepted – prihvaćeno: 13. 12. 2021.

UDK: 630*86; 676.01; 676.1

<https://doi.org/10.5552/drind.2022.2112>

© 2022 by the author(s).

Licensee Faculty of Forestry and Wood Technology, University of Zagreb.

This article is an open access article distributed under the terms and conditions of the Creative Commons Attribution (CC BY) license.

ABSTRACT • Kraft pulping as the dominant pulping method contributes to several environmental problems. To overcome these problems, environmentally friendly pulping methods have been investigated. In the last years, deep eutectic solvents (DESs) have been identified as up-and-coming reagents in the lignocellulosic material processing and they are characterized as environmentally friendly. This study investigated the use of DES in pulp production from European black poplar chips. The DES mixture was prepared from choline chloride (ChCl) and ethylene glycol (EG). In addition, traditional soda and kraft pulping methods were carried out with poplar chips for comparison with the DES pulps. It was found that pulp production from poplar chips using DES was comparable to the soda and kraft pulps in terms of pulp yield, pulp viscosity, and opacity. The DES pulps easily reached target pulp freeness levels. However, the strength properties and brightness of the DES pulps were lower than those of the soda and kraft pulps. The strength properties of DES pulps can be improved with paper strength enhancers such as starch and micro or nanofibrillated cellulose. Also, the utilization of DES in pulp production may have an important role in cleaner production and it represents a greener alternative to traditional pulp production methods.

KEYWORDS: DES; European black poplar; green chemistry; cleaner production; pulp properties

SAŽETAK • Celuloza se najčešće proizvodi kraft postupkom koji je povezan s nekoliko ekoloških problema. Kako bi se ti problemi prevladali, istražene su ekološki prihvatljive metode proizvodnje celuloze. Posljednjih su godina duboka eutektička otapala (DES) prepoznata kao ekološki prihvatljivi reagensi za preradu lignoceluloznih materijala u budućnosti. U ovom je radu istraživana uporaba DES-a u proizvodnji celuloze od sječke drva europske crne topole. DES smjesa pripremljena je od kolin-klorida (ChCl) i etilen-glikola (EG). Osim toga, tradicionalnim je natronskim i kraft postupkom proizvedena celuloza od sječke drva topole radi usporedbe s celulozom proizvedenom s dodatkom DES smjese. Utvrđeno je da je celuloza proizvedena od sječke drva topole uz upotrebu DES-a u smislu prinosa, viskoznosti i neprozirnosti usporediva s celulozom dobivenom natronskim i kraft postupkom. Celuloza proizvedena uz dodatak DES-a lako je dosegla ciljani stupanj slobode celuloze. Međutim, svojstva čvrstoće i svjetlina celuloze proizvedene uz dodatak DES-a bili su lošiji od tih svojstava natronske i kraft celuloze. Svojstva čvrstoće DES celuloze mogu se poboljšati pojačivačima čvrstoće papira kao što su škrob i mikrofibrilirana ili nanofibrilirana celuloza. Osim toga, upotreba DES-a u proizvodnji celuloze može imati važan doprinos čistijoj proizvodnji i čini zeleniju alternativu tradicionalnim metodama proizvodnje celuloze.

KLJUČNE RIJEČI: DES; europska crna topola; zelena kemija; čistija proizvodnja; svojstva celuloze

¹ Authors are researchers at Bartın University, Forestry Faculty, Forest Industry Engineering, Bartın, Turkey.

1 INTRODUCTION

1. UVOD

Although kraft pulping is the dominant method used in pulp industry, it has some serious disadvantages such as air pollution, water pollution, and high investment costs (Muurinen, 2000). For this reason, a number of new pulp processing methods have been studied. Organosolv (solvent-based) pulping is a chemical pulping method having minimum environmental impact, high pulp yield, and low investment costs (Saberikhan *et al.*, 2011). EG pulping has been carried out with various biomasses such as palm oil tree residues (Alriols *et al.*, 2009), olive tree trimmings (Jiménez *et al.*, 2004), birch (Gast and Puls, 1984; Rutkowski *et al.*, 1993), aspen and beech (Rutkowski *et al.*, 1993), tagasaste (Jiménez *et al.*, 2008; Rodríguez *et al.*, 2008), vine shoots (Rodríguez *et al.*, 2008; Jiménez *et al.*, 2009), cotton stalks and leucaena (Rodríguez *et al.*, 2008), pine (Nakamura and Takauti, 1941), and larch (Uraki and Sano, 1999).

Deep eutectic solvents (DESs) consist of a mixture of at least two components: a hydrogen-bond acceptor (HBA) and a hydrogen-bond donor (HBD) (Pena-Pereira and Namieśnik, 2014). They are non-toxic, eco-friendly, easily prepared, inexpensive, readily available, biodegradable, and recyclable green solvents. Because of these extraordinary advantages, interest in DESs continues to grow (Zhang *et al.*, 2012). The usage potential for DESs in organic synthesis, electrochemistry, catalysis, and biology has been studied (Škulcová *et al.*, 2016). In addition, DESs have been extensively used in the field of separation technologies (Hou *et al.*, 2018). The solubilizing capacity of DESs on lignocellulosic biomass or its individual components such as lignins was tested by Francisco *et al.* (2012). Since then, studies related to biomass processing using various DESs have received increasing attention (Alvarez-Vasco *et al.*, 2016; Hou *et al.*, 2018; Chen *et al.* 2019; Jablonsky *et al.* 2019; Oh *et al.* 2020; Soto-Salcido *et al.* 2020).

A number of studies have focused on DES treatment using several types of lignocellulosic biomass. De Dios (2013) studied lignin isolation from wheat straw and pine sawdust using several deep eutectic mixtures and reported that the lignin solubility was increased with the higher content of lactic acid in DES. Abougor (2014) pretreated switchgrass with ChCl/trifluoroacetamide and lignin content was reduced by 6.66 %. In addition, they noted that pretreatment did not cause a reduction in cellulose and hemicellulose content. The wheat straw was pretreated with ChCl based DESs and containing different HBDs such as urea, lactic acid, malic acid, malonic acid, and oxalic acid dehydrate by Jablonsky *et al.* (2015). The highest lignin re-

moval was 57.9 % with ChCl/oxalic acid dihydrate at 60 °C and 24 h. Kumar *et al.* (2016) investigated solubility of cellulose, xylan, and lignin from rice straw in DESs containing ChCl, betaine, and lactic acid. Their experiments revealed that xylan and cellulose are not soluble in DESs. The lignin solubility in DES consisting lactic acid/ChCl reached almost 100 %. The lignin removal in the lactic acid/betaine (5:1) was 38 %. Alvarez-Vasco *et al.* (2016) used ChCl based DESs for lignin extraction from Douglas-fir and poplar wood. The lignin amounts removed from biomass with ChCl/lactic acid treatment were 78 % in poplar and 58 % in Douglas-fir. The isolation of willow lignin with the treatment of DESs (ChCl/lactic acid, ChCl/urea, ChCl/glycerol) was evaluated by Li *et al.* (2017). Optimal DES-lignin yield (91.8 %) was obtained at a ChCl/lactic acid molar ratio of 1:10, extraction time of 12 h, and temperature of 120 °C. Pan *et al.* (2017) focused on the effects of DES (ChCl/urea) pretreatment on holocellulose, α -cellulose, and acid-insoluble-lignin contents of rice straw. They observed that ChCl/urea had a selective delignification. Lynam *et al.* (2017) noted that DESs (lactic acid/betaine, lactic acid/ChCl, lactic acid/proline, formic acid/ChCl, and acetic acid/ChCl) were capable of selectively dissolving the lignin at 60 °C. Zulkefli *et al.* (2017) noted that the pretreatment of oil palm trunk with ethylammonium chloride/EG had removed 42 % lignin and 83 % hemicellulose. Hou *et al.* (2018) also reported that DES consisting of ChCl/urea could effectively delignify from the rice straw. Chen and Wan (2018) noted that lignin was recoverable with high purity after microwave-assisted DES pretreatment of Miscanthus, switchgrass, and corn stover. Kiliç-Pekgözlü and Ceylan (2019) extracted the Scots pine wood with several DESs. They found that DESs could be alternative solvents for organic solvents. Recently, the effects of DESs (ChCl/lactic acid and ChCl/glycerin) treatment on the chemical composition of the sapwood and heartwood of red pine were investigated by Kwon *et al.* (2020). They observed that the solid residue yield after DES treatment decreased with increasing HBD concentration and treatment time. In addition, the solid residue amount in the sapwood was higher compared to the heartwood.

DESs have potential applications in the pulp and paper industry. Choi *et al.* (2016a and 2016b, respectively) investigated the effects of DES treatment of thermomechanical pulp (TMP) and bleached chemithermomechanical pulp (BCTMP) on handsheet properties. Majová *et al.* (2017a) reported the effect of initial kappa number of kraft pulp on the DES pulp delignification efficiency, and determined that kraft pulp having higher kappa number was more easily delignified with DES. A recent study found that DES could be replaced by oxygen in kraft pulp delignifica-

tion (Majová *et al.*, 2017b). The hardwood kraft pulp was delignified using two different DESs (ChCl/lactic acid and alanine/lactic acid) and the effects of DES delignification on the chemical and physical properties of the kraft pulp were investigated (Jablonsky *et al.*, 2018). The potential of potassium carbonate/glycerol (K_2CO_3 /Gly) DES applied as a green solvent in rice straw pulping was evaluated by Lim *et al.* (2019). Smink *et al.* (2019) investigated the effect of ChCl on the pulping of *Eucalyptus globulus* chips. Rapeseed stems, corn stalks, and wheat straw were treated with acidic and alkaline DESs and the effect of DES type on nanocelluloses properties and on the resulting nanopapers was investigated by Suopajarvi *et al.* (2020). Recently, the effect of ChCl based DES treatment on the chemical composition of the low-energy mechanical pulp was reported by Fiskari *et al.* (2020).

Although several DESs have been extensively studied for pretreating biomass, the literature available regarding the use of DESs in pulp production is limited. To the best of our knowledge, to date, no investigation has been carried out comparing DES pulp production with traditional pulping methods. Therefore, the aim of this study was to evaluate the usage possibilities of a DES (ChCl:EG) in pulp production from poplar wood and to compare DES pulping with traditional pulping methods. The effects of different ChCl:EG molar ratios (4:10, 5:10, 6:10) were also investigated in this study.

2 MATERIALS AND METHODS

2. MATERIJALI I METODE

2.1 Material

2.1.1. Materijal

European black poplar (*Populus nigra* L.) was chosen as the wood material because it has a rapid growth rate and provides easier delignification compared to softwoods. A 10 cm-thick wood disc was taken at breast height from a poplar log originating from Bartın Province (Turkey). This disc was debarked and subdivided into four discs (25 mm-thick). These were manually chipped, using a chisel, as homogeneously as possible to 25 mm × 15 mm × 5 mm in size for pulping.

2.2 Chemical composition and fiber morphology of poplar wood

2.2.1. Kemijski sastav i morfologija vlakana topolovine

The chemical analysis of poplar wood was carried out according to TAPPI T 257 cm-02. The klason lignin content (TAPPI T 222 om-02), α -cellulose content (TAPPI T 203 cm-09), and holocellulose content (Wise and Karl, 1962) of the poplar wood were determined according to the relevant methods. The cold-hot water, ethanol, and 1 % NaOH solubilities of the poplar

were also determined according to TAPPI T 207 cm-99, TAPPI T 204 cm-97, and TAPPI T 212 om-02, respectively. In addition, poplar wood chips were macerated with the chlorite method (Spearin and Isenberg, 1947). After maceration, the fiber length (L) and width (D), lumen width (d), and cell wall thickness (w) of fibers were measured. The slenderness ratio (L/D), flexibility ratio [$(d/D) \times 100$], and Runkel ratio [$(2 \times w)/d$] were calculated from the dimensional measurements of fibers.

2.3 DES preparation

2.3.1. Priprema DES-a

DES was prepared by mixing ChCl with EG. All chemicals were acquired commercially (Merck) and used as received. The ChCl and EG were mixed in different mole ratios (4:10, 5:10, and 6:10) and used as DES. The solution was heated at 100 °C for 60 min. until a transparent liquid retaining no solid particles was formed. The mixture was stored in a desiccator until use after being cooled to room temperature.

2.4 DES and traditional pulping

2.4.1. DES i tradicionalna proizvodnja celuloze

DES and traditional pulping conditions are shown in Table 1. In DES cookings, the oven-dried (o.d.) poplar chip weight was calculated for each cooking experiment using the ChCl/EG molar ratio and cooking liquor/chip ratio. In DES-1 (4ChCl/10EG), 558.48 g ChCl (ChCl molecular weight × 4) and 620.7 g EG (EG molecular weight × 10) were used. The total weight of ChCl and EG was 1179.18 g. The o.d. poplar chip weight in the 2.5/1 cooking liquor/chip was 471.73 g (1179.18/2.5). According to the same calculation, 527.52 g and 583.37 g o.d. poplar chips were used in DES-2 (5ChCl/10EG) and DES-3 (6ChCl/10EG) cooking experiments, respectively (Table 1).

The air-dried poplar wood chips were cooked in a rotary digester. After cooking, the DES pulps and traditional pulps were washed to remove the black liquor with tap water. The DES pulps were also washed in ethanol. All pulps were disintegrated in a laboratory-type pulp mixer with 2-L capacity. The pulps were screened with a Somerville-type pulp screen according to TAPPI T 275 sp-02. After screening, all the pulp samples were beaten to 25 °SR and 35 °SR in a Valley Beater according to TAPPI T 200 sp-15.

2.5 Pulp and paper properties

2.5.1. Svojstva celuloze i papira

The screened yield (TAPPI T 210 cm-02), kappa number (TAPPI T 236 om-99), viscosity (SCAN-CM 15-62), and freeness of the pulps (ISO 5267-1) were determined. The handsheets (75 g/m²) were made by a Rapid-Kothen Sheet Former (ISO 5269- 2) at three different freeness levels (unbeaten, 25 °SR, and 35 °SR).

Table 1 DES and traditional pulping conditions**Tablica 1.** DES i tradicionalni uvjeti proizvodnje celuloze

Pulps <i>Celuloza</i>	ChCl/EG mole ratios in cooking <i>ChCl/EG molarni omjer pri kuhanju</i>	Active alkali <i>Aktivna lužina</i>	Sulfidity <i>Sulfidnost</i>	Wood weight in cooking, o.d. <i>Masa drva pri kuhanju, o.d.</i>	Liquor/wood ratio <i>Omjer tekućina/drvo</i>	Cooking time to max. temp., min <i>Vrijeme kuhanja do najviše temperature, min</i>	Cooking time at max. temp., min <i>Vrijeme kuhanja pri najvišoj temperaturi, min</i>	Cooking temp., °C <i>Temperatura kuhanja, °C</i>
DES-1	4ChCl/10EG	-	-	471.67	2.5/1	60	150	190
DES-2	5ChCl/10EG	-	-	527.52	2.5/1	60	150	190
DES-3	6ChCl/10EG	-	-	583.37	2.5/1	60	150	190
Soda	-	18	-	700	4/1	60	60	170
Kraft	-	16	20	700	4/1	60	60	170

Table 2 Chemical composition and fiber morphology of poplar wood**Tablica 2.** Kemijski sastav i morfologija vlakana topolovine

Experiments / <i>Eksperimenti</i>	<i>Populus nigra</i>	<i>Populus tremula</i> (Gulsoy and Tufek, 2013)
Holocellulose, % / <i>Holoceceluloza, %</i>	81.25	82.68
α -cellulose, %	46.30	49.03
Klason lignin, %	18.51	16.69
Ethanol solubility, % / <i>Topljivost u etanolu, %</i>	2.22	3.22
1 % NaOH solubility, % / <i>Topljivost u 1-postotnom NaOH, %</i>	14.65	15.34
Hot water solubility, % / <i>Topljivost u vrućoj vodi, %</i>	3.59	3.04
Cold water solubility, % / <i>Topljivost u hladnoj vodi, %</i>	2.18	1.73
Fiber length, mm / <i>Duljina vlakana, mm</i>	1.05	1.10
Fiber width, μm / <i>Širina vlakana, μm</i>	27.47	23.90
Lumen width, μm / <i>Širina lumena, μm</i>	15.53	11.40
Cell wall thickness, μm / <i>Debljina stanične stijenke, μm</i>	5.97	6.30
Slenderness ratio / <i>Omjer vitkosti</i>	38.22	46.00
Flexibility ratio / <i>Omjer fleksibilnosti</i>	56.53	47.70
Runkel ratio / <i>Runkelov omjer</i>	0.77	1.10

After conditioning in accordance with TAPPI T 402 sp-03, the tensile index, stretch, and tensile energy absorption (TEA) (ISO 1924-3), tear index (TAPPI T 414 om-98), burst index (TAPPI T 403 om-02), opacity (TAPPI T 519 om-02), and brightness (TAPPI T 525 om-02) of the handsheets were determined.

2.6 Statistical analysis

2.6. Statistička analiza

The data related to properties of the DES, kraft, and soda pulps from poplar chips were analyzed using analysis of variance (ANOVA) and the Duncan test at a 95 % confidence level ($p < 0.05$). The effects of the methods and conditions of pulping on the paper properties were evaluated statistically using SPSS software. In Figures 2-8, the same letters on the columns denote no statistically significant differences between the groups. In addition, there were no significant differences among the values with the same letters in the same column of Table 3 and Table 4.

3 RESULTS AND DISCUSSION

3. REZULTATI I RASPRAVA

The results of the chemical composition analysis and fiber morphology of the *Populus nigra* wood are presented in Table 2. These results are similar to those of *Populus tremula*.

The pulp properties of DES, soda, and kraft pulps are presented in Table 3. The screened yield of the DES pulps was higher than that of the soda and kraft pulps. The highest screened yield was obtained from DES-3 pulp. The screened yields of the DES pulps after washing with ethanol were similar to those of the traditional pulps (Table 3).

The effect of ChCl molar ratio on kappa number of DES pulp was insignificant ($p > 0.05$). The kappa numbers of DES pulps were higher than for the traditional pulps ($p < 0.05$). This result can be ascribed to the insufficient delignification of DES pulping compared to the traditional pulping methods. Alvarez-Vas-

Table 3 Pulp properties of DES, soda, and kraft pulps**Tablica 3.** Svojstva DES celuloze, natronske i kraft celuloze

Pulps <i>Celuloza</i>	Screened yield, % <i>Prinos prosjavanja, %</i>	Reject, % <i>Škart, %</i>	Total yield, % <i>Ukupan prinos, %</i>	Weight loss at washing, % <i>Gubitak mase pri ispiranju, %</i>	Screened yield after washing, % <i>Prinos prosija- vanja nakon ispiranja, %</i>	Total yield after washing, % <i>Ukupan prinos nakon ispiranja, %</i>	Kappa number <i>Kappa broj</i>	Viscosity, cm ³ /g <i>Viskoznost, cm³/g</i>
DES-1	52.02	9.27	61.29	14.29	44.59	53.86	72.55a*	1154a
DES-2	49.07	2.47	51.54	14.65	41.88	44.35	69.52a	1170a
DES-3	52.78	5.46	58.24	17.22	43.69	49.15	70.47a	1199a
Soda	40.65	7.81	48.46	-	-	-	37.40b	1126a
Kraft	46.42	17.31	63.73	-	-	-	41.08b	1185a


*There were no significant differences among the values with the same letters in the same column. / Nema značajnih razlika između vrijednosti s istim slovom unutar istog stupca.

co *et al.* (2016) reported that DESs can selectively cleave ether bonds without affecting the C-C linkages in lignin and can facilitate lignin extraction from wood fibers. Choi *et al.* (2016a) treated thermomechanical pulp (TMP) with DES (lactic acid and betaine) and identified a linear correlation between the delignification of the TMP and the molar ratio of lactic acid in DES. Yiin *et al.* (2016) noted that the lignin solubility capacity of DES was improved with the increased molar ratio of HBA. Majová *et al.* (2017a) noted that the kappa number of kraft pulp decreased from 21.7 to 12.3 with alanine/lactic acid treatment. Jablonsky *et al.* (2018) reported that the kappa number of untreated hardwood kraft pulp was reduced from 21.7 to 13.5 with ChCl/lactic acid treatment and to 12.3 with alanine/ lactic acid treatment. Lim *et al.* (2019) found that the lignin content in rice straw significantly decreased after DES (K₂CO₃/Gly) pulping. Fiskari *et al.* (2020) stated that DESs consisting of ChCl/lactic acid, ChCl/urea, and ChCl/ oxalic acid reduced the lignin content of Asplund fibers by approximately 50 %. On

the other hand, the viscosity of the DES, soda, and kraft pulps had similar values ($p > 0.05$). Majová *et al.* (2017a) reported that the viscosity of kraft pulp decreased slightly, from 789 to 784 ml/g, with alanine/ lactic acid treatment.

Pulp refinability (beatability) is a significant parameter in terms of energy consumption of a pulp mill and usually depends on the chemical composition of the pulps (Gulsoy and Eroglu, 2011). Pulp beating consumes up to 15-18 % of the total electric energy used for paper production (Bajpai *et al.*, 2006; Cui *et al.*, 2015). Therefore, the pulp should reach the desired freeness level as soon as possible. DES pulps easily reached 25 °SR and 35 °SR freeness levels despite their higher kappa numbers (Table 3, Figure 1). DES-2 pulp reached 25 °SR in 240 s., whereas soda pulp reached the same freeness level in 660 s. DES-1 pulp and soda pulp reached 35 °SR in 420 s and 900 s, respectively.

The tensile index of the unbeaten and beaten DES pulps was significantly lower ($p < 0.05$) than that of the traditional pulps (Figure 2). In the unbeaten, 25

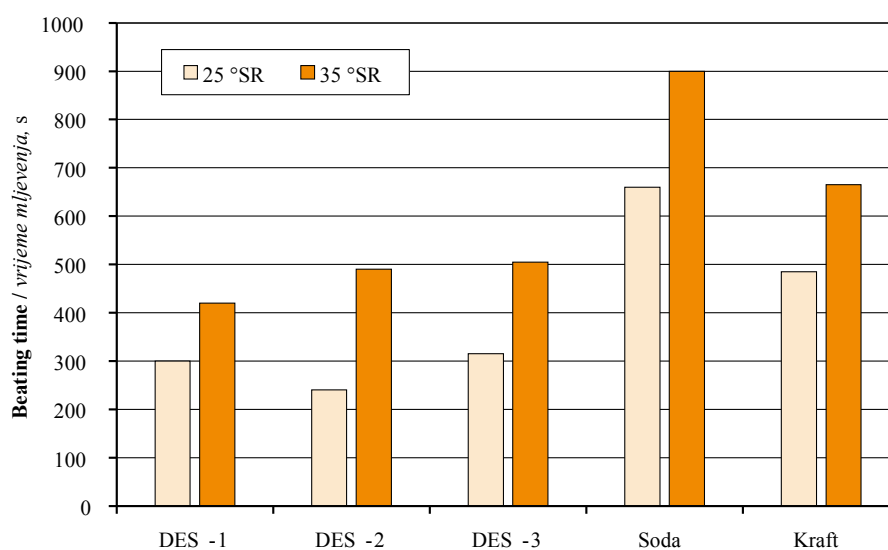**Figure 1** Beating time required for a given freeness level of DES, soda, and kraft pulps**Slika 1.** Vrijeme mljevenja potrebno za dani stupanj slobode DES celuloze, natronske i kraft celuloze

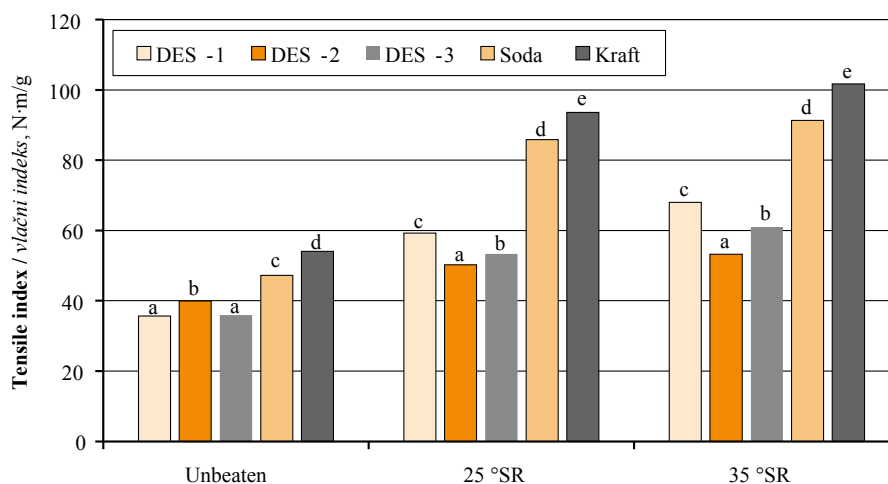


Figure 2 Tensile index of DES, soda, and kraft pulps (The same letters on the columns denote no statistically significant differences between the groups)

Slika 2. Vlačni indeks DES celuloze, natronske i kraft celuloze (ista slova iznad stupaca znače da nema statistički značajne razlike među skupinama)

°SR and 35 °SR DES pulps, the highest tensile index was determined in DES-2, DES-1, and DES-1 pulps as 39.94, 59.24, and 68.02 N·m/g, respectively. The highest tensile index values in the unbeaten, 25 °SR and 35 °SR DES pulps compared to the soda and kraft pulps, respectively, were lower by 15.42 % and 26.17% (unbeaten pulp), 30.98 % and 36.72 % (25 °SR pulp), and 25.47 % and 33.12 % (35 °SR pulp). At all pulp freeness levels, the highest tensile index values were obtained with kraft pulp. Moreover, the tensile index of the DES pulps was irregularly affected by the ChCl amount in the DES cooking liquor. The tensile index of the DES pulps was significantly increased with beating ($p < 0.05$) (Table 4). However, the tensile index increases due to beating were a little more obvious in the traditional pulps. For example, the tensile index of DES-1 pulp was increased by 66.26 % and 90.91 % with beating to 25 °SR and 35 °SR, respectively. In the soda and kraft pulps, these

values were 81.77 % & 93.29 % and 73.03 % & 87.99 %, respectively.

The stretch values of the unbeaten DES pulps were higher than those of the traditional pulps, whereas the stretch values of the beaten DES pulps were lower than those of the traditional pulps (Figure 3, $p < 0.05$). In the unbeaten pulps, the highest and the lowest stretch values were obtained from DES-2 pulp and soda pulp as 1.37 % and 0.85 %, respectively. On the other hand, the stretch values of the unbeaten and 25 °SR DES pulps were irregularly affected by the ChCl amount in the DES cooking liquor. In the 35 °SR pulps, the effect on stretch of the ChCl amount in the DES cooking liquor was statistically insignificant ($p > 0.05$). Stretch values of the DES pulps, as for the traditional pulps, were significantly increased with beating ($p < 0.05$) (Table 4).

In the unbeaten pulps, the highest TEA value was 28.86 J/m² (DES-2 pulp). In the 25 °SR and 35 °SR

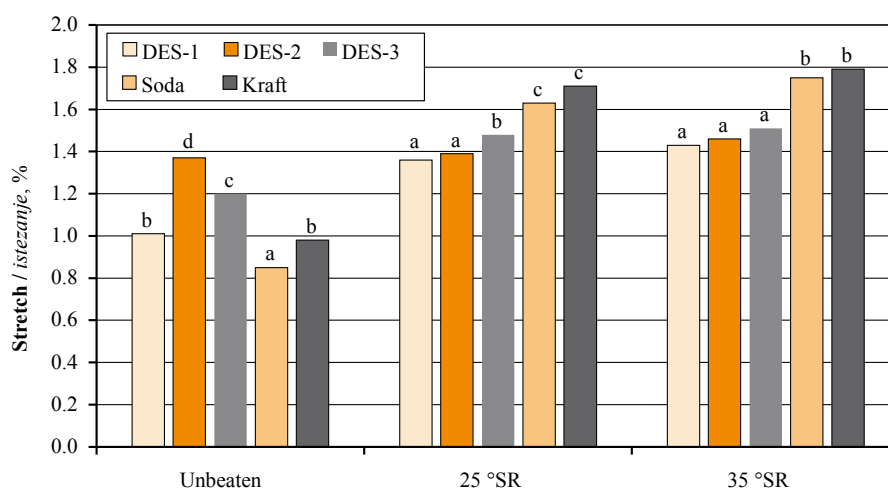


Figure 3 Stretch of DES, soda, and kraft pulps

Slika 3. Istezanje DES celuloze, natronske i kraft celuloze

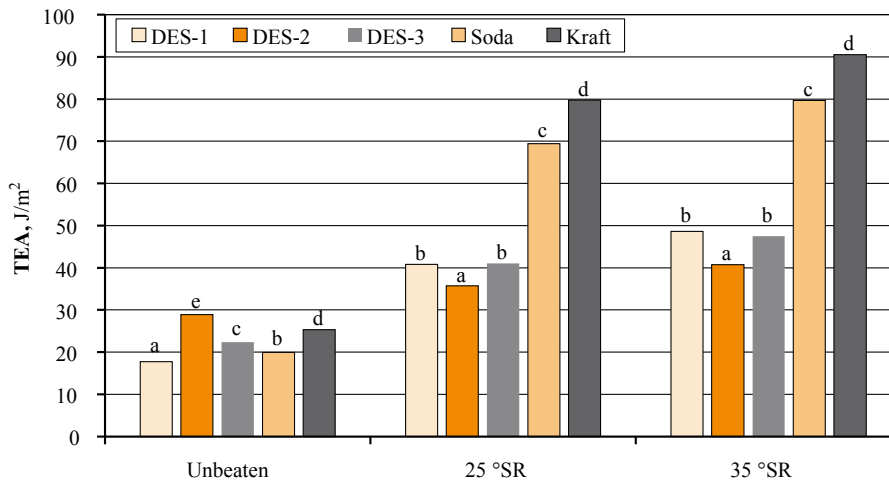


Figure 4 TEA of DES, soda, and kraft pulps

Slika 4. TEA za DES celulozu, natronsku i kraft celulozu

pulps, the stretch values of DES pulps were lower than those of soda and kraft pulps (Figure 4, $p < 0.05$). Moreover, the TEA of DES pulps changed irregularly with the rising ChCl amount in the DES cooking liquor. The pulp beating had a positive effect on the TEA values of DES and traditional pulps (Table 4). However, the effect of beating on TEA was more pronounced in the traditional pulps.

In the unbeaten and beaten pulps, the tear index values of the DES pulps were lower than those of the soda and kraft pulps ($p < 0.05$). The highest tear index values of the DES pulps were determined in DES-3 pulp samples. At all pulp freeness levels, the effect on the tear index of the ChCl amount in the DES cooking liquor was statistically insignificant (Figure 5, $p > 0.05$). In terms of the tear index, the response of DES pulps to beating was different from that of traditional pulps. The tear index increased when the traditional pulps were beaten up to 25 °SR. With increasing beating levels, their tear index values decreased. In contrast, the

tear index values of the DES pulps regularly decreased with increasing beating levels (Table 4).

The burst index values of the unbeaten samples of DES-2, soda, and kraft pulps were 1.54, 1.38, and 1.62 $\text{kPa}\cdot\text{m}^2/\text{g}$. The burst index values of the DES pulps were lower than those of the soda and kraft pulps except for the unbeaten DES-2 pulp (Figure 6). The burst index values of the unbeaten and 35 °SR pulps varied irregularly with increasing ChCl amounts in the cooking liquor. However, the decrease in the burst index with increasing ChCl amount was insignificant ($p > 0.05$). The relationship between the burst index of DES pulps and increasing pulp beating levels was linear ($p < 0.05$) (Table 4). However, the tensile index increases after pulp beating were more pronounced in the traditional pulps. For example, the burst index of DES-1 pulp was increased by 71.09 % and 97.66 % with beating to 25 °SR and 35 °SR, respectively. The burst index increases with beating in the soda and kraft pulps were 152.17 and 181.16 % and 138.27 and 161.11 %, respectively.

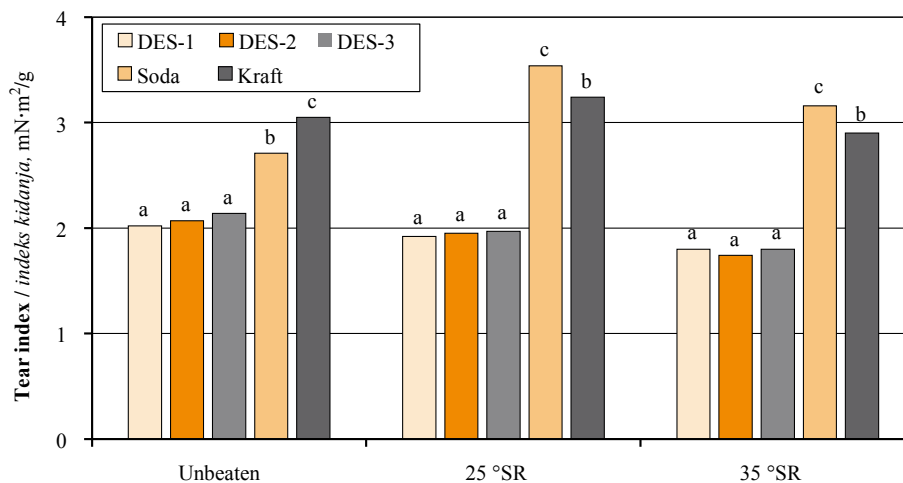


Figure 5 Tear index of DES, soda, and kraft pulps

Slika 5. Indeks kidanja DES celuloze, natronske i kraft celuloze

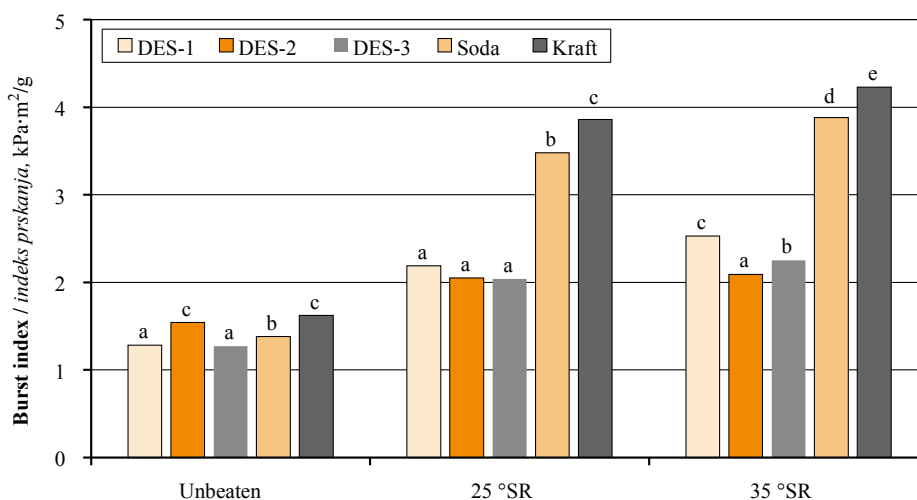


Figure 6 Burst index of DES, soda, and kraft pulps

Slika 6. Indeks prskanja DES celuloze, natronske i kraft celuloze

Choi *et al.* (2016a) reported that the burst and tensile indices of TMP pulps increased when a higher molar ratio of lactic acid was used in the DES preparation. The authors also reported that the tear index of TMP pulps was reduced with the increasing molar ratio of lactic acid in the DES. Jablonsky *et al.* (2018) noted that the burst, tensile, and tear indices of untreated hardwood kraft pulp decreased with ChCl/lactic acid and alanine/lactic acid treatment. Untreated Asplund fiber pulp had a higher or equal tensile index compared to DES-treated pulp at all pulp freeness levels (Fiskari *et al.*, 2020). Suopajarvi *et al.* (2020) stated that nanopapers from alkaline DES-treated wheat straw, rapeseed stems, and corn stalks had better tensile strength and strain compared with nanopapers from acidic DESs.

At all pulp freeness levels, the DES pulp had lower brightness values compared to soda and kraft pulps (Figure 7) because of the higher kappa numbers and insufficient delignification of the DES pulps (Table 3). Pulp brightness was significantly reduced with the

increase of ChCl in the DES ($p < 0.05$). In addition, the brightness of DES-1 pulp was reduced with beating, whereas for DES-2 and DES-3 pulps, the changes were irregular (Table 4). As expected, the brightness of kraft and soda pulps was reduced with beating. This result can be explained by the homogeneous lignin distribution of the DES fibers in the cell walls.

In the unbeaten and beaten samples, the DES pulp exhibited higher opacity values compared to the soda and kraft pulps (Figure 8). The effect of the amount of ChCl in DES on pulp opacity was statistically insignificant ($p > 0.05$). Although the opacity of the traditional pulps changed with beating ($p < 0.05$), the opacity of the DES pulps did not change ($p > 0.05$) (Table 4). This experiment demonstrated that, compared to traditional pulping methods, DES pulping had a negative effect on pulp brightness, although it had a positive effect on pulp opacity. Choi *et al.* (2016a) noted that lactic acid and betaine DES treatment had no effect on the optical properties of TMP pulp. An in-

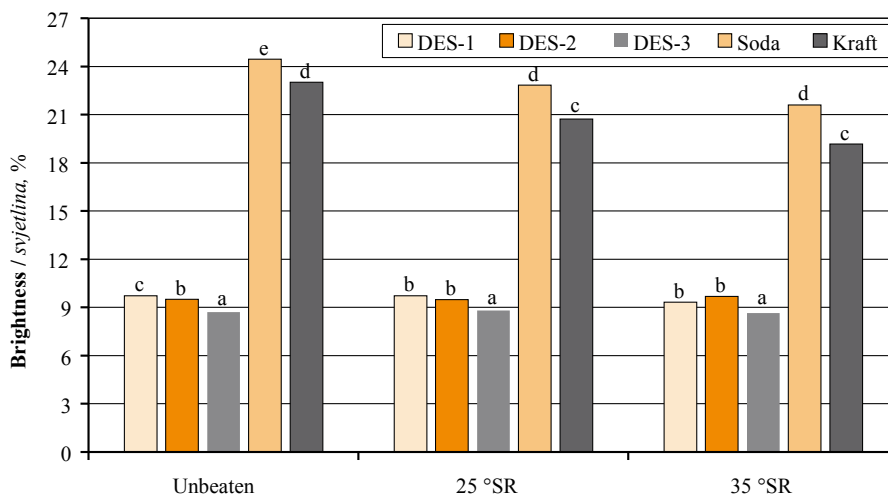


Figure 7 Brightness of DES, soda, and kraft pulps

Slika 7. Svjetlina DES celuloze, natronske i kraft celuloze

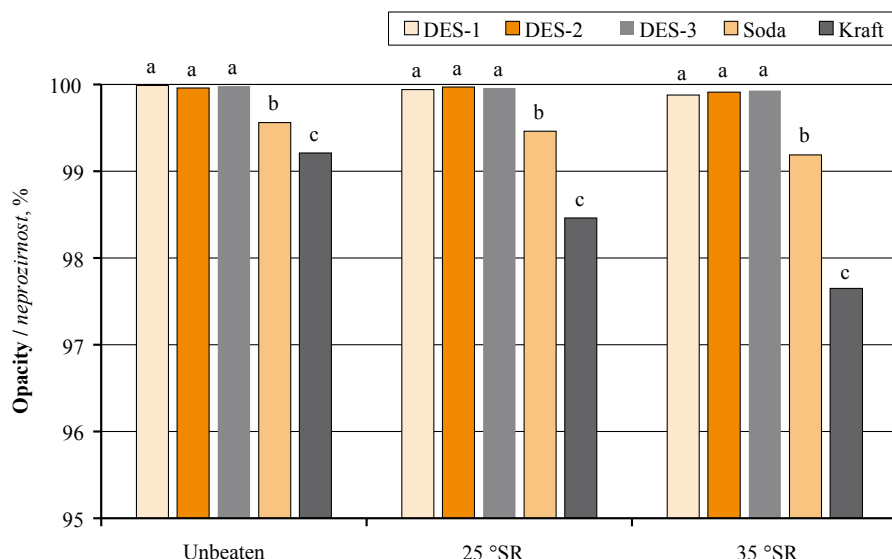


Figure 8 Opacity of DES, soda, and kraft pulps

Slika 8. Neprozirnost DES celuloze, natronske i kraft celuloze

crease in the brightness of kraft pulp was observed with DES treatment (Škulcová *et al.*, 2017). Jablonsky *et al.* (2018) reported that the brightness of untreated hardwood kraft pulp increased from 27.02 to 34.05 with ChCl/lactic acid treatment and to 33.38 with alanine/lactic acid treatment.

4 CONCLUSIONS

4. ZAKLJUČAK

In this new century, sustainable development challenges pulp and paper industry to develop new and cleaner technological processes. DESs have potential

applications in the pulp and paper industry. The novelty of this study is the utilization of DES in pulp production and comparison of traditional pulps and DES pulps. The results of this study showed that the use of DES was an effective method for the pulping of poplar lignocellulosic biomass (*Populus nigra* L.). The DES formed by ChCl and EG (molar ratios = 4:10, 5:10, 6:10) applied at 190 °C for 3.5 h enabled pulp production from poplar chips. The DES pulps were comparable to those produced by traditional pulping methods in terms of pulp yield, pulp viscosity, and opacity. The DES-1 pulp exhibited the best cooking conditions in terms of total pulp yield. On the other hand, the beata-

Table 4 Effect of beating level on handsheet properties of DES, soda, and kraft pulps

Tablica 4. Utjecaj stupnja mljevenja na svojstva ručno izrađenog papira od DES celuloze, natronske i kraft celuloze

Pulps Celuloza	Freeness, °SR Stupanj slobode, °SR	Tensile index, N·m/g Vlačni indeks, N·m/g	Stretch, % Istezanje, %	TEA, J/m ²	Tear index, mN·m ² /g Indeks kidanja, mN·m ² /g	Burst index, kPa·m ² /g Indeks prskanja	Brightness, % Svjetlina, %	Opacity, % Neprozir- nost, %
DES-1	15	35.63a*	1.01a	17.76a	2.02a	1.28a	9.73a	99.99a
	26	59.24b	1.36b	40.79b	1.92a	2.19b	9.72a	99.94a
	37	68.02c	1.43b	48.60c	1.80b	2.53c	9.33b	99.88a
DES-2	17	39.94a	1.37a	28.86a	2.07a	1.54a	9.51a	99.96a
	25	50.26b	1.39a	35.69b	1.95a	2.05b	9.48a	99.97a
	35	53.28c	1.46a	40.69c	1.74b	2.09b	9.68b	99.91a
DES-3	16	35.91a	1.20a	22.36a	2.14a	1.27a	8.71a	99.98a
	25	53.33b	1.48b	41.00b	1.97b	2.04b	8.80a	99.96a
	35	61.02c	1.51b	47.47c	1.80c	2.25c	8.64a	99.93a
Soda	12	47.22a	0.85a	19.92a	2.71a	1.38a	24.46a	99.56a
	25	85.83b	1.63b	69.43b	3.54c	3.48b	22.84b	99.46a
	36	91.27c	1.75b	79.66c	3.16b	3.88c	21.61c	99.19b
Kraft	12	54.10a	0.98a	25.34a	3.05a	1.62a	23.03a	99.21a
	24	93.61b	1.71b	79.70b	3.24c	3.86b	20.73b	98.46b
	35	101.70c	1.79b	90.50c	2.90b	4.23c	19.16c	97.65c

*There were no significant differences among the values with the same letters in the same column. / Nema značajnih razlika među vrijednostima s istim slovom unutar istog stupca.

bility of the pulp was positively affected by the DES pulping. However, the strength properties and brightness of the DES pulps were lower than those of the traditional pulps. In the unbeaten and beaten DES pulps, the highest strength values were obtained from the DES-2 and DES-1 pulps.

This study demonstrated that DES composed of ChCl and EG can be used as green solvent for pulp production from biomass. It can be readily applicable to pulp production. The DES pulping process is an alternative to traditional pulping due to its low-environmental-impact. Inexpensive and biodegradable DESs, used in pulping, are characterized as economically and environmentally viable solvents. These solvents could offer unique opportunities for cleaner pulp production. Therefore, in order to reveal true potential of DESs and to improve pulp properties, further research is needed on the use of DESs as green solvents in pulping.

Acknowledgements – Zahvala

The authors thank the Scientific Research Fund of Bartın University for its financial support (Project Number: 2017-FEN-CY-011).

5 REFERENCES

5. LITERATURA

- Abougor, H., 2014: Utilization of deep eutectic solvent as a pretreatment option for lignocellulosic biomass. PhD Thesis, Tennessee Technological University.
- Alriols, M. G.; Tejado, A.; Blanco, M.; Mondragon, I.; Labidi, J., 2009: Agricultural palm oil tree residues as raw material for cellulose, lignin and hemicelluloses production by ethylene glycol pulping process. *Chemical Engineering Journal*, 148: 106-114. <https://doi.org/10.1016/j.cej.2008.08.008>
- Alvarez-Vasco, C.; Ma, R.; Quintero, M.; Guo, M.; Geleynse, S.; Ramasamy, K. K.; Wolcott, M.; Zhang, X., 2016: Unique low-molecular-weight lignin with high purity extracted from wood by deep eutectic solvents (DES): A source of lignin for valorization. *Green Chemistry*, 18 (19): 5133-5141. <https://doi.org/10.1039/C6GC01007E>
- Bajpai, P.; Mishra, S. P.; Mishra, O. P.; Kumar, S.; Bajpai, P. K., 2006: Use of enzymes for reduction in refining energy-laboratory studies. *TAPPI Journal*, 5: 25-31.
- Chen, Z.; Wan, C., 2018: Ultrafast fractionation of lignocellulosic biomass by microwave-assisted deep eutectic solvent pretreatment. *Bioresource Technology*, 250: 532-537. <https://doi.org/10.1016/j.biortech.2017.11.066>
- Chen, Y.; Zhang, L.; Yu, J.; Lu, Y.; Jiang, B.; Fan, Y.; Wang, Z., 2019: High-purity lignin isolated from poplar wood meal through dissolving treatment with deep eutectic solvents. *Royal Society Open Science*, 6: 181757. <https://doi.org/10.1098/rsos.181757>
- Choi, K. H.; Lee, M. K.; Ryu, J. Y., 2016a: Effect of molar ratios of DES on lignin contents and handsheets properties of thermomechanical pulp. *Journal of Korea TAPPI*, 48: 28-33. <https://doi.org/10.7584/ktappi.2016.48.2.028>
- Choi, K. H.; Nam, Y. S.; Lee, M. K.; Ryu, J. Y., 2016b: Changes of BCTMP fibers and handsheets properties by the treatment of LB DES at different molar ratios. *Journal of Korea TAPPI*, 48: 75-81. <https://doi.org/10.7584/ktappi.2016.48.1.075>
- Cui, L.; Meddeb-Mouelhi, F.; Laframboise, F.; Beauregard, M., 2015: Effect of commercial cellulases and refining on kraft pulp properties: Correlations between treatment impacts and enzymatic activity components. *Carbohydrate Polymers*, 115: 193-199. <https://doi.org/10.1016/j.carbpol.2014.08.076>
- De Dios, S. L. G., 2013: Phase equilibria for extraction processes with designer solvents. PhD Thesis, University of Santiago De Compostela.
- Francisco, M.; van den Bruinhorst, A.; Kroon, M. C., 2012: New natural and renewable low transition temperature mixtures (LTTMs): screening as solvents for lignocellulosic biomass processing. *Green Chemistry*, 14: 2153-2157. <https://doi.org/10.1039/C2GC35660K>
- Fiskari, J.; Ferritsius, R.; Osong, S. H.; Persson, A.; Höglund, T.; Immerzeel, P.; Norgren, M., 2020: Deep eutectic solvent delignification to low-energy mechanical pulp to produce papermaking fibers. *BioResources*, 15: 6023-6032.
- Gast, D.; Puls, J., 1984: Ethylene glycol-water pulping. Kinetics of delignification, in: Ferrero, G. L. (ed.), *Anaerobic Digestion and Carbohydrate Hydrolysis of Waste*. Elsevier, Essex, pp. 450-453.
- Gulsoy, S. K.; Eroglu, H., 2011: Influence of sodium borohydride on kraft pulping of European black pine as a digester additive. *Industrial & Engineering Chemistry Research*, 50: 2441-2444. <https://doi.org/10.1021/ie101999p>
- Gulsoy, S. K.; Tufek, S., 2013: Effect of chip mixing ratio of *Pinus pinaster* and *Populus tremula* on kraft pulp and paper properties. *Industrial & Engineering Chemistry Research*, 52(6): 2304-2308. <https://doi.org/10.1021/ie302709e>
- Hou, X. D.; Li, A. L.; Lin, K. P.; Wang, Y. Y.; Kuang, Z. Y.; Cao, S. L., 2018: Insight into the structure-function relationships of deep eutectic solvents during rice straw pretreatment. *Bioresource Technology*, 249: 261-267. <https://doi.org/10.1016/j.biortech.2017.10.019>
- Jablonský, M.; Škulcová, A.; Kamenská, L.; Vrška, M.; Šima, J., 2015: Deep eutectic solvents: fractionation of wheat straw. *BioResources*, 10: 8039-8047.
- Jablonsky, M.; Majova, V.; Skulcova, A.; Haz, A., 2018: Delignification of pulp using deep eutectic solvents. *Journal of Hygienic Engineering and Design*, 22: 76-81.
- Jablonsky, M.; Haz, A.; Majova, V., 2019: Assessing the opportunities for applying deep eutectic solvents for fractionation of beech wood and wheat straw. *Cellulose*, 26: 7675-7684. <https://doi.org/10.1007/s10570-019-02629-0>
- Jiménez, L.; Rodríguez, A.; Díaz, M. J.; Lopez, F.; Ariza, J., 2004: Organosolv pulping of olive tree trimmings by use of ethylene glycol/soda/water mixtures. *Holzforschung*, 58: 122-128. <https://doi.org/10.1515/HF.2004.017>
- Jiménez, L.; Perez, A.; De la Torre, M. J.; Rodríguez, A.; Angulo, V., 2008: Ethyleneglycol pulp from tagasaste. *Bioresource Technology*, 99: 2170-2176. <https://doi.org/10.1016/j.biortech.2007.05.044>
- Jiménez, L.; Angulo, V.; Rodríguez, A.; Sánchez, R.; Ferrer, A., 2009: Pulp and paper from vine shoots: Neural fuzzy modeling of ethylene glycol pulping. *Bioresource Technology*, 100: 756-762. <https://doi.org/10.1016/j.biortech.2008.07.019>
- Kiliç-Pekgözlü, A.; Ceylan, E., 2019: Application of DES (deep eutectic solvents) to wood extractives. *Wood Industry and Engineering*, 1: 52-56.

24. Kumar, A. K.; Parikh, B. S.; Pravakar, M., 2016: Natural deep eutectic solvent mediated pretreatment of rice straw: bioanalytical characterization of lignin extract and enzymatic hydrolysis of pretreated biomass residue. *Environmental Science and Pollution Research*, 23: 9265-9275. <https://doi.org/10.1007/s11356-015-4780-4>
25. Kwon, G. J.; Yang, B. S.; Park, C. W.; Bandi, R.; Lee, E. A.; Park, J. S.; Han, S. Y.; Kim, N. H.; Lee, S. H., 2020: Treatment effects of choline chloride-based deep eutectic solvent on the chemical composition of red pine (*Pinus densiflora*). *BioResources*, 15: 6457-6470.
26. Li, T.; Lyu, G.; Liu, Y.; Lou, R.; Lucia, L. A.; Yang, G.; Chen, J.; Saeed, H. A. M., 2017: Deep eutectic solvents (DESS) for the isolation of willow lignin (*Salix matsudana* cv. Zhuliu). *International Journal of Molecular Sciences*, 18: 2266. <https://doi.org/10.3390/ijms18112266>
27. Lim, W. L.; Gunny, A. A. N.; Kasim, F. H.; AlNashef, I. M.; Arbain, D., 2019: Alkaline deep eutectic solvent: a novel green solvent for lignocellulose pulping. *Cellulose*, 26: 4085-4098. <https://doi.org/10.1007/s10570-019-02346-8>
28. Lynam, J. G.; Kumar, N.; Wong, M. J., 2017: Deep eutectic solvents' ability to solubilize lignin, cellulose, and hemicellulose; thermal stability; and density. *Bioresource Technology*, 238: 684-689. <https://doi.org/10.1016/j.biortech.2017.04.079>
29. Majová, V.; Horanová, S.; Škulcová, A.; Šíma, J.; Jablonský, M., 2017a: Deep eutectic solvent delignification: Impact of initial lignin. *BioResources*, 12: 7301-7310.
30. Majová, V.; Jablonský, M.; Strizincová, P.; Škulcová, A.; Vrška, M., 2017b: Replacement of oxygen delignification by use of deep eutectic solvents. FP1306 COST Action, Third Workshop & Fourth MC Meeting, Torremolinos, 27-28 March 2017, P28.
31. Muurinen, E., 2000: Organosolv pulping: A review and distillation study related to peroxyacid pulping. PhD Thesis, University of Oulu.
32. Nakamura, H.; Takauti, E., 1941: Zellstoffherstellung mittels aethylenglykol. *Cellulose Industry*, 17: 19-26. <https://doi.org/10.2115/fiber1925.17.en19>
33. Oh, Y.; Park, S.; Jung, D.; Oh, K. K.; Lee, S. H., 2020: Effect of hydrogen bond donor on the choline chloride-based deep eutectic solvent-mediated extraction of lignin from pine wood. *International Journal of Biological Macromolecules*, 165: 187-197. <https://doi.org/10.1016/j.ijbiomac.2020.09.145>
34. Pan, M.; Zhao, G.; Ding, C.; Wu, B.; Lian, Z.; Lian, H., 2017: Physicochemical transformation of rice straw after pretreatment with a deep eutectic solvent of choline chloride/urea. *Carbohydrate Polymers*, 176: 307-314. <https://doi.org/10.1016/j.carbpol.2017.08.088>
35. Pena-Pereira, F.; Namieśnik, J., 2014: Ionic liquids and deep eutectic mixtures: sustainable solvents for extraction processes. *ChemSusChem*, 7: 1784-1800. <https://doi.org/10.1002/cssc.201301192>
36. Rodríguez, A.; Pérez, A.; de la Torre, M. J.; Ramos, E.; Jiménez, L., 2008: Neural fuzzy model applied to ethylene-glycol pulping of non-wood raw materials. *Bioresource Technology*, 99: 965-974. <https://doi.org/10.1016/j.biortech.2007.03.007>
37. Rutkowski, J.; Mroz, W.; Surna-Slusarska, B.; Perlinkasipa, K., 1993: Glycolic delignification of hardwood. In: *Progress 93 Conference Proceeding*, 1: 190-205.
38. Saberikhah, E.; Mohammadi Rovshandeh, J.; Reza-yati-Charan, P., 2011: Organosolv pulping of wheat straw by glycerol. *Cellulose Chemistry and Technology*, 45: 67-75.
39. Smink, D.; Juan, A.; Schuur, B.; Kersten, S. R., 2019: Understanding the role of choline chloride in deep eutectic solvents used for biomass delignification. *Industrial & Engineering Chemistry Research*, 58: 16348-16357. <https://doi.org/10.1021/acs.iecr.9b03588>
40. Soto-Salcido, L. A.; Anugwom, I.; Ballinas-Casarrubias, L.; Mänttari, M.; Kallioinen, M., 2020: NADES-based fractionation of biomass to produce raw material for the preparation of cellulose acetates. *Cellulose*, 27: 6831-6848. <https://doi.org/10.1007/s10570-020-03251-1>
41. Spearin, W. E.; Isenberg, I. H. 1947: Maceration of woody tissue with acetic acid and sodium chlorite. *Science*, 105: 214-214. <https://doi.org/10.1126/science.105.2721.214>
42. Suopajärvi, T.; Ricci, P.; Karvonen, V.; Ottolina, G.; Liimatainen, H., 2020: Acidic and alkaline deep eutectic solvents in delignification and nanofibrillation of corn stalk, wheat straw, and rapeseed stem residues. *Industrial Crops and Products*, 145: 111956. <https://doi.org/10.1016/j.indcrop.2019.111956>
43. Škulcová, A.; Kamenská, L.; Kalman, F.; Ház, A.; Jablonský, M.; Čížová, K.; Šurina, I., 2016: Deep eutectic solvents as medium for pretreatment of biomass. *Key Engineering Materials*, 688: 17-24. <https://doi.org/10.4028/www.scientific.net/KEM.688.17>
44. Škulcová, A.; Majová, V.; Šíma, J.; Jablonský, M., 2017: Mechanical properties of pulp delignified by deep eutectic solvents. *BioResources*, 12: 7479-7486.
45. Uraki, Y.; Sano, Y., 1999: Polyhydric alcohol pulping at atmospheric pressure: An effective method for organosolv pulping of softwoods. *Holzforschung*, 53: 411-415. <https://doi.org/10.1515/HF.1999.068>
46. Wise, L. E.; Karl, H. L., 1962: *Cellulose and Hemicellulose in Pulp and Paper Science and Technology*. McGraw Hill Book Co., New York.
47. Yiin, C. L.; Quitain, A. T.; Yusup, S.; Sasaki, M.; Uemura, Y.; Kida, T., 2016: Characterization of natural low transition temperature mixtures (LTTMs): Green solvents for biomass delignification. *Bioresource Technology*, 119: 258-264. <https://doi.org/10.1016/j.biortech.2015.07.103>
48. Zhang, Q.; Vigier, K. D. O.; Royer, S.; Jerome, F., 2012: Deep eutectic solvents: Syntheses, properties and applications. *Chemical Society Reviews*, 41: 7108-7146. <https://doi.org/10.1039/C2CS35178A>
49. Zulkefli, S.; Abdulmalek, E.; Rahman, M. B. A., 2017: Pretreatment of oil palm trunk in deep eutectic solvent and optimization of enzymatic hydrolysis of pretreated oil palm trunk. *Renew. Energy*, 107: 36-41. <https://doi.org/10.1016/j.renene.2017.01.037>
50. ***ISO 1924-3, 2005: Paper and board – Determination of tensile properties. Part 3: Constant rate of elongation method (100 mm/min). ISO, Geneva, Switzerland.
51. ***ISO 5267-1, 1999: Pulps – Determination of drainability. Part 1: Schopper-Riegler method. ISO, Geneva, Switzerland.
52. ***ISO 5269-2, 2004: Pulps – Preparation of laboratory sheets for physical testing. Part 2: Rapid-Köthen method. ISO, Geneva, Switzerland.
53. ***SCAN-CM 15-62, 1962: Viscosity of cellulose in cupriethylenediamine solution (CED). SCAN, Stockholm, Sweden.
54. ***TAPPI T 200 sp-15, 2015: Laboratory Beating of Pulp (Valley Beater Method). TAPPI, Atlanta, GA, USA.
55. ***TAPPI T 203 cm-09, 2009: Alpha-, beta- and gamma-cellulose in pulp. TAPPI, Atlanta, GA, USA.

56. ***TAPPI T 204 cm-97, 1997: Solvent extractives of wood and pulp. TAPPI, Atlanta, GA, USA.
57. ***TAPPI T 207 cm-99, 1999: Water solubility of wood and pulp. TAPPI, Atlanta, GA, USA.
58. ***TAPPI T 210 cm-03, 2003: Sampling and testing wood pulp shipments for moisture. TAPPI, Atlanta, GA, USA.
59. ***TAPPI T 212 om-02, 2002: One percent sodium hydroxide solubility of wood and pulp. TAPPI, Atlanta, GA, USA.
60. ***TAPPI T 222 om-02, 2002: Acid-insoluble lignin in wood and pulp. TAPPI, Atlanta, GA, USA.
61. ***TAPPI T 236 om-99, 1999: Kappa number of pulp. TAPPI, Atlanta, GA, USA.
62. ***TAPPI T 257 cm-02, 2002: Sampling and preparing wood for analysis. TAPPI, Atlanta, GA, USA.
63. ***TAPPI T 275 sp-02, 2002: Screening of pulp (Somerville-type equipment). TAPPI, Atlanta, GA, USA.
64. ***TAPPI T 402 sp-03, 2003: Standard conditioning and testing atmospheres for paper, board, pulp handsheets, and related products. TAPPI, Atlanta, GA, USA.
65. ***TAPPI T 403 om-15, 2015: Bursting strength of paper. TAPPI, Atlanta, GA, USA.
66. ***TAPPI T 414 om-98, 1998: Internal tearing resistance of paper (Elmendorf-type method). TAPPI, Atlanta, GA, USA.
67. ***TAPPI T 519 om-02, 2002: Diffuse opacity of pulp. TAPPI, Atlanta, GA, USA.
68. ***TAPPI T 525 om-02, 2002: Diffuse brightness of pulp. TAPPI, Atlanta, GA, USA.

Corresponding address:

Assoc. Prof. SEZGIN KORAY GÜLSOY

Bartın University, Forestry Faculty, 74100, Bartın, TURKEY, e-mail: sgulsoy@bartin.edu.tr