



Open Access : : ISSN 1847-9286

<https://pub.iapchem.org/ojs/index.php/JESE>

Original scientific paper

Perspective on the mechanism of mass transport-induced (tip-growing) Li dendrite formation by comparing conventional liquid organic solvent with solid polymer-based electrolytes

Lukas Stolz¹, Martin Winter^{1,2} and Johannes Kasnatscheew^{1,✉}

¹ MEET Battery Research Center, Institute of Physical Chemistry, University of Münster, Corrensstraße 46, 48149 Münster, Germany

² Helmholtz-Institute Münster, IEK-12, Forschungszentrum Jülich GmbH, Corrensstraße 46, 48149 Münster, Germany

Corresponding author: ✉ j.kasnatscheew@uni-muenster.de

Received: February 27, 2023; Accepted: July 31, 2023; Published: August 9, 2023

Abstract

A major challenge of Li metal electrodes is the growth of high surface area lithium during Li deposition with a variety of possible shapes and growing mechanisms. They are reactive and lead to active lithium losses, electrolyte depletion and safety concerns due to a potential risk of short-circuits and thermal runaway. This work focuses on the mechanism of tip-growing Li dendrite as a particular high surface area lithium morphology. Its formation mechanism is well-known and is triggered during concentration polarization, i.e. during mass (Li^+) transport limitations, which has been thoroughly investigated in literature with liquid electrolytes. This work aims to give a stimulating perspective on this formation mechanism by considering solid polymer electrolytes. The in-here shown absence of the characteristic “voltage noise” immediately after complete concentration polarization, being an indicator for tip-growing dendritic growth, rules out the occurrence of the particular tip-growing morphology for solid polymer electrolytes under the specific electrochemical conditions. The generally poorer kinetics of solid polymer electrolytes compared to liquid electrolytes imply lower limiting currents, i.e. lower currents to realize complete concentration polarization. Hence, this longer-lasting Li-deposition times in solid polymer electrolytes are assumed to prevent tip-growing mechanism via timely enabling solid electrolyte interphase formation on fresh Li deposits, while, as stated in previous literature, in liquid electrolytes, Li dendrite tip-growth process is faster than solid electrolyte interphase formation kinetics. It can be reasonably concluded that tip-growing Li dendrites are in general practically unlikely for both, (i) the lower conducting electrolytes like solid polymer electrolytes due to enabling solid electrolyte interphase formation and (ii) good-conducting electrolytes like liquids due to an impractically high current required for concentration polarization.

Keywords

Mass transport limitation; Li metal battery; concentration polarization; liquid electrolyte

Introduction

Li metal-based rechargeable batteries (LMBs) gain enhanced attention in battery R&D owing to higher theoretical specific and volumetric energies compared to conventional Li ion batteries (LIBs) [1-6]. However, the hazardous formation of high surface area lithium (HSAL) morphologies, *e.g.* mossy and dendritic Li, limits their application [2,4,7-9]. HSAL is reactive and leads to capacity losses, electrolyte depletion [2,9,10], as well as a potential safety risks *via*, *e.g.*, short circuits, which can be typically detected *via* an electrochemical voltage noise response,[11-14] also in Li ion batteries [8,15-18]. Many research efforts have been conducted towards mechanistic understanding of HSAL formation and growth, in particular in regard to the morphology of deposited Li [7,8,19-23].

A well-known HSAL-type is the tip-growing Li dendrite which grows immediate after complete concentration polarization, *i.e.* after complete limitation of (Li⁺) mass transport towards Li metal electrode and can be electrochemically indicated *via* a voltage noise behavior [24-26]. In that scenario, dendrite growth relates with complete Li⁺ depletion at the Li|electrolyte interface resulting in tip-growing Li dendrite propagation. It can be described as a process counteracting complete concentration polarization, leading to an over-limiting current [24-27]. This mechanism has been derived and studied for liquid organic solvent-based electrolytes, where, due to the good kinetic aspects, harsh electrochemical conditions are required, *e.g.* elevated currents and/or long inter-electrode distances to realize complete concentration polarization [26].

In this work, the aim is to give a perspective on mechanistical validation and understanding of the Li-growth mechanism with the generally poorer ion-conducting solid polymer-based electrolytes [2,28-31] under complete concentration polarization conditions, first introduced by Brissot *et al.* [32].

Discussion

Complete concentration polarization: Mass transport limitation in battery electrolytes

When applying a moderate current in Li metal batteries, extra Li⁺ is provided and consumed at the anode|electrolyte and cathode|electrolyte interface, respectively [26,33,34]. As a result, a Li salt concentration gradient emerges throughout the electrolyte and reaches a steady-state after a certain time while evoking Li⁺ transport *via* diffusion (Fick's laws). At kinetically harsher conditions, *e.g.* higher currents, low temperature and/or large electrolyte thickness, the applied current can force continuous growth in concentration gradient up to the maximum, *i.e.* complete Li⁺ depletion at the cathode|electrolyte interface [33-36]. This 'complete concentration polarization' obeys Sand's equation and its vertical-type polarization (overvoltage) starts at a defined Sand time [26,34]. The limiting current, defining the threshold for complete concentration polarization, is a characteristic value of DIC electrolytes and depends on Li⁺ diffusion coefficient, Li⁺ salt concentration and electrolyte thickness [33-35]. These relations can be simply validated in symmetric Li | Li cells as depicted in Figure 1.

A strategy to counteract this issue relies on the use of electrolytes with high Li⁺ transference numbers (immobile anions), *e.g.* single-ion conducting (SIC) electrolytes [1,37-41], that counteract the concentration polarization by enhanced migration for reasons of charge neutrality. The impact of SICs on Li deposition is discussed later.

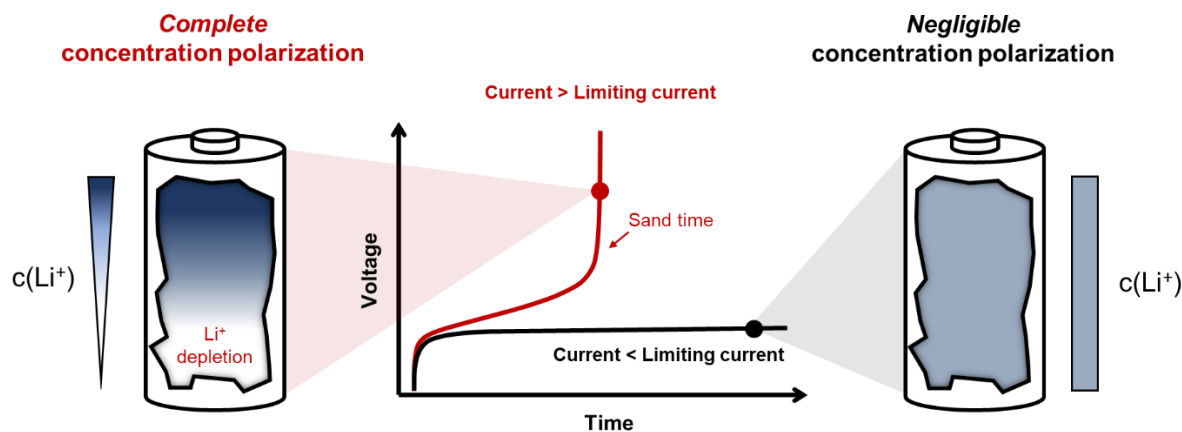


Figure 1. Schematic illustration of the complete concentration polarization seen at a characteristic Sand time, which proceeds when applied current exceeds the limiting current (redrawn from [37])

Complete concentration polarization: The onset of dendritic Li deposition in liquid electrolyte-based batteries

In the case of good ion conducting liquid electrolytes, e.g. 1 M LiPF₆ in a mixture of ethylene carbonate (EC) and dimethyl carbonate (DMC) [2,42-44], concentration polarization can only be observed beyond practical operating conditions, e.g. under impractically high currents and/or large electrolyte thickness. Bai *et al.* [26] could visually observe complete concentration polarization *via* the onset of dendritic Li deposition in symmetric Li | Li cells inside glass capillaries with an effective electrolyte thickness of about 7 mm in this model cell compared to a practical separator thickness of ~0.02 mm in real cells as depicted in Figure 2 [26]. It is demonstrated, that the onset of complete concentration polarization marks the transition between mossy and dendritic Li deposition [26]. The latter is regarded as deposition morphology occurring during over-limiting current phenomena, which circumvents Li⁺ depletion and is observable by a noisy voltage response immediately after the Sand time (Figures 2a and 2 b) [26]. It has been reported, that mossy Li deposition is a root-growing phenomenon, where Li plating occurs preferably below the protective solid electrolyte interphase (SEI), while dendritic Li deposition proceeds tip-growing preferably above the SEI (Figure 2c) due to higher growing rate compared SEI formation rate, as stated in literature [24,26].

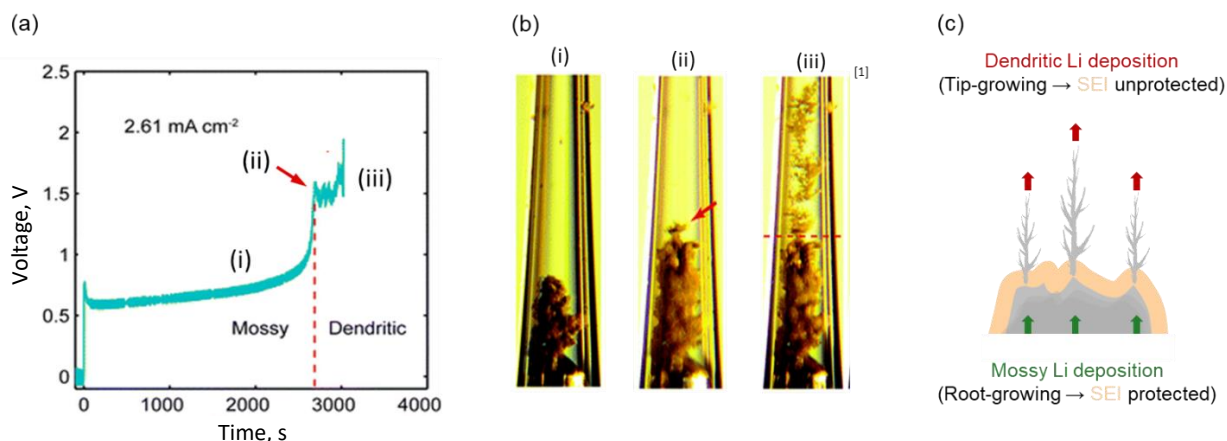


Figure 2. (a) Voltage as a function of time for an over-limiting current in glass capillary-based Li | Li cell with liquid electrolyte (1M LiPF₆ in EC/DMC), derived from Bai *et al.*[26] (b) Visual observation of the onset of complete concentration polarization (ii) and immediate transition from mossy (root-growing) to dendritic (tip-growing) Li deposition (iii), derived from Bai *et al.*[26] (c) Schematic illustration of tip-growing (dendritic) and root-growing (mossy) Li deposition, which among others differs in the presence of SEI on the high surface are lithium (HSAL), depending on HSAL growth kinetics relative to SEI formation kinetics.[24,26] (redrawn from [26])

No impact of complete concentration polarization on dendritic Li deposition in solid polymer electrolytes (SPEs)

Because of considerably poorer kinetic transport properties (*e.g.* lower diffusion coefficients), thus lower limiting currents, observing the concentration polarization in SPEs is practically easier than in liquid electrolytes and can be investigated in conventional cell configuration with conventional *inter*-electrode distances, *e.g.* coin cells [34,45]. Interestingly, contrary to the observations derived by Bai *et al.* for liquid organic electrolytes, the SPE, *i.e.* solid poly(ethylene) oxide (PEO)/Lithium bis(trifluoromethanesulfonyl)imide (LiTFSI), within Li|Li cells proceeds without the characteristic voltage noise immediately after concentration polarization, as shown Figure 3a [32-37]. It can be concluded that a direct transition from mossy Li towards tip-growing dendritic Li is absent with this type of electrolyte. A reason might be an interplay/competition between the rate of Li deposition and rate of SEI growth, which has been suggested by Bai *et al.* [26] for liquid electrolytes (Figure 3b) [24,26]. A requirement for dendritic (tip-growing) Li deposition is a higher rate of deposition (according to the applied current rate) compared to the rate of SEI growth, as otherwise the SEI would passivate the metallic Li deposits and lead to probably mossy (root-growing) Li morphologies, as stated in literature [24]. Hence, it is speculated that the tip-growing dendritic Li deposition might be less favored with SPEs as a consequence of rather lower limiting current, *i.e.* longer lasting deposition times.

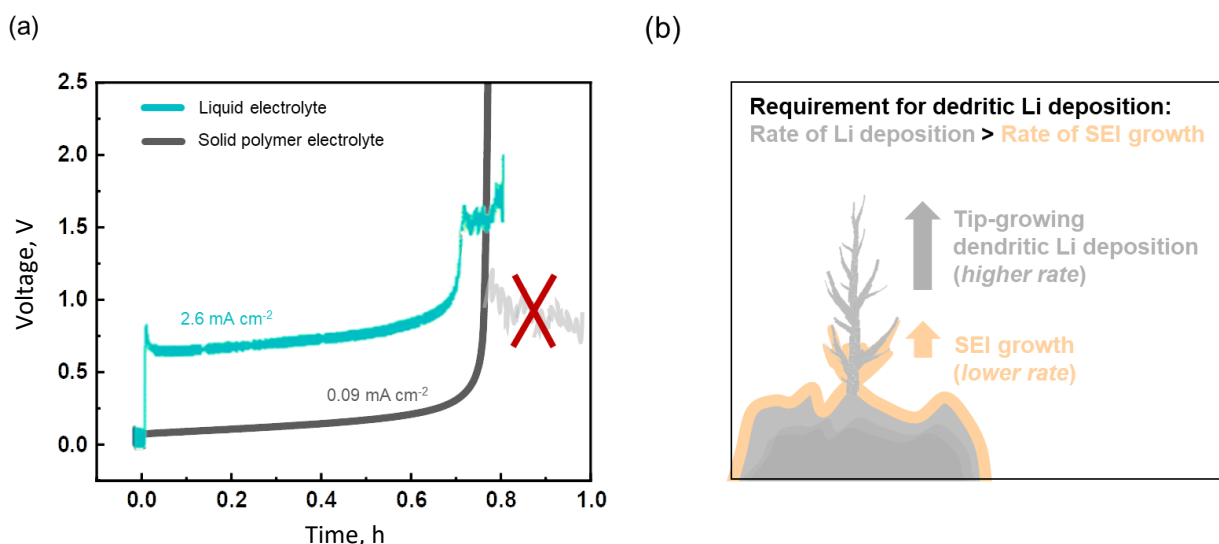


Figure 3. (a) Voltage as a function of time for over-limiting currents in liquid electrolyte (Bai *et al.* [26]) vs. SPE-based Li|Li cells. Complete concentration polarization initiates an onset of dendritic (tip-growing) Li deposition in liquid electrolytes, seen as voltage noise, while such voltage response is missing with SPE. Missing voltage noise points to absence of dendritic Li in SPE [26,34], (b) which is assumed to relate with lower rates (lower limiting currents), which realize sufficient time for SEI growth on the Li deposits, consequently leading to different HSAL shapes (redrawn from [26])

Interestingly, Brissot *et al.* [32] detect a change in Li plating morphology at high currents, suggesting dendritic Li deposition, though, it is not observed in the first mass transport limiting polarization, *i.e.* first cycle (as seen in liquids), but only after subsequent cycling. This is probably caused by local defects in the SEI. A theoretical possible difference might be also related with electroconvection [24,27,46]. where overpotentials required for tip-based dendritic growth might be significantly higher compared to liquid-based systems due to structural rigidity of SPEs. However, practically they are not observable in voltage ranges up to 10 V, which is significantly higher than voltage ranges in conventional batteries (<5 V); thus relativizing its practical relevance.

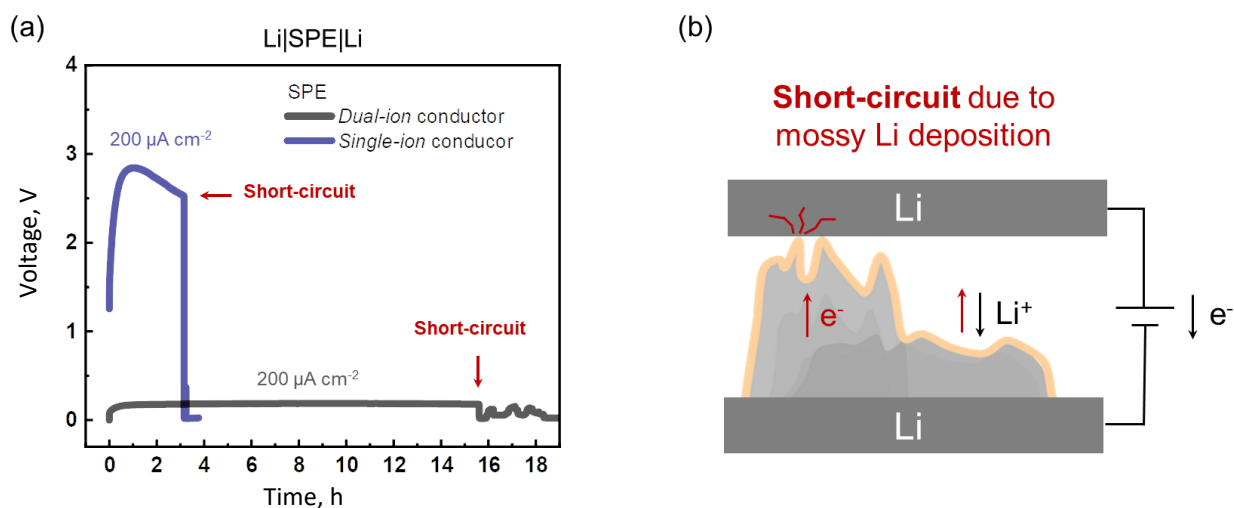


Figure 4. (a) Voltage as a function of time at moderate areal current ($200 \mu\text{A g}^{-1}$) of DIC- and SIC-SPE-based symmetric Li|Li cells, both leading to short-circuits.[37] (b) As schematically illustrated, short circuits are likely caused by inhomogeneous mossy Li depositions and growth throughout the SPE after several hours

Still, short-circuits based on inhomogeneous Li deposition are still relevant in SPEs and happen also below the limiting currents, *i.e.* below onset of complete mass transport limitations/concentration polarizations [11-14]. Though, tip-growing dendritic Li is practically unlikely, other HSAL morphologies like mossy Li deposition still play a major role and also can lead to short circuits *via* penetration as they obviously cannot be mechanically suppressed by the flexible SPE membranes as depicted in Figure 4 for SIC and DIC electrolytes in symmetric Li|Li cells.

The insufficient suppression in HSAL penetration/short-circuits of SPE- compared to liquid electrolyte-based battery cells is likely due to rather poor mechanical stability [12,14] combined with lack in homogeneity (*e.g.* salt distribution), which consequently enhance the risk of inhomogeneous plating [11], thus the growth throughout the SPE-based membrane [13].

Oxidative SPE decomposition is unlikely, as the Li^+ depletion occurs at the negative electrode; also, no signs of decomposition (*e.g.* potential plateau) are observable, as would be the case during electrochemical decomposition [14,47,48].

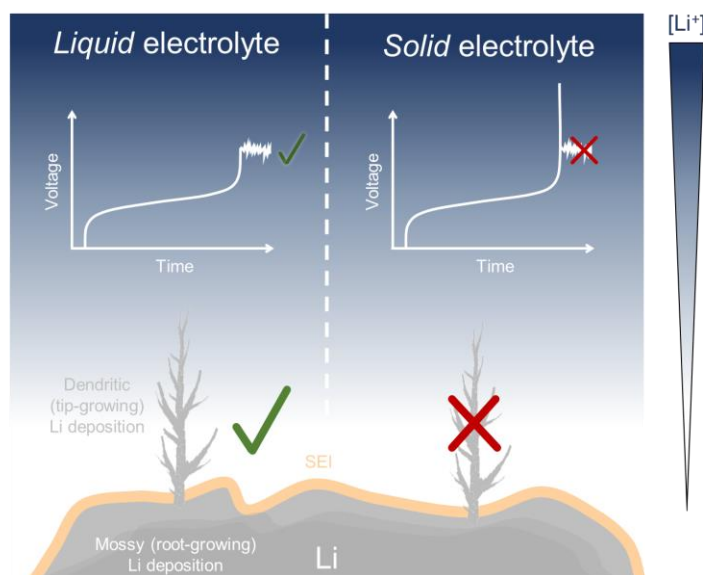


Figure 5. Schematic comparison of Li interface in contact with liquid- and solid electrolyte at mass-transport limiting (*i.e.*, Li^+ depleted) conditions. The tip-growing Li dendrite in liquid electrolytes, seen by characteristic voltage noise, is absent in solid electrolytes

Conclusion and future perspective

Lithium metal electrodes can potentially raise the energy density and specific energy compared to Li ion batteries, but suffer from growth of reactive HSAL during charge/discharge cycling. Drawbacks like electrolyte depletion, capacity losses, safety issues and short-circuits require intense R&D efforts.

In literature, a complete Li⁺ (mass) transport limitation, that is, complete concentration polarization is linked to the onset of a particular HSAL shape, *i.e.* dendritic (tip-growing) Li deposition and has been thoroughly investigated in Li|Li cells with liquid organic solvent-based electrolytes. This HSAL shape is indicated by the characteristic over-limiting current and seen *via* voltage noise [24,26].

Interestingly, with SPEs this particular voltage noise is absent during the complete concentration polarization, pointing to absence of dendritic tip-growing Li growth under the applied specific electrochemical conditions [33-35,37], as summarized in Figure 5. Given the poorer ion transport properties of SPEs compared to liquid electrolytes [28,31,49], the considerably lower limiting current/rate in SPEs [33,34] is suggested to provide sufficient time for formation of SEI on freshly deposited Li, thus being a crucial difference to the literature known situation in liquid electrolytes, where the rate of Li tip-growing is faster than the rate of SEI formation [24,26]. Still, dendritic Li deposition has been observed in SPE-based systems as discussed by Brissot *et al.* [32], but only after subsequent cycling, probably due to defects in the SEI [32,50], in other words, not observed in the initial charge as is seen for liquid-based electrolytes.

It can be concluded, that tip-growing dendritic morphology is generally unlikely in Li metal batteries with both, (i) good-conducting electrolytes (*e.g.* liquid) as impractically high currents and/or *inter*-electrode distances are necessary to achieve complete concentration polarization [26], or (ii) poor-conducting electrolytes (*e.g.* SPEs) as the rate of tip-growing mechanism is slower than the SEI-formation rate, as also stated in literature [24].

Still, short-circuits, most likely due to mossy Li penetration, are still an issue and observed for dual ion conducting (DIC)- and single ion conducting (SIC)-SPE-based Li battery cells [37]. These insights suggest that developing electrolytes with higher cation transference number is not expedient for suppression of the particular tip-growing Li dendrite. Other factors like mechanical stability of SPE and/or homogeneity aspects of Li deposition, have likely a stronger effect [11].

Acknowledgements: Financial support from the German Federal Ministry for Education and Research (BMBF) within the project, MEET Hi-End III (03XP0258A) as part of the ExcellBattMat Cluster is gratefully acknowledged.

References

- [1] J. Janek, W.G. Zeier, A Solid Future for Battery Development, *Nature Energy* **1** (2016) 16141. <https://doi.org/10.1038/nenergy.2016.141>
- [2] X. Wu, K. Pan, M. Jia, Y. Ren, H. He, L. Zhang, S. Zhang, Electrolyte for lithium protection: From liquid to solid, *Green Energy & Environment* **4** (2019) 360-374. <https://doi.org/10.1016/j.gee.2019.05.003>
- [3] M.S. Whittingham, Lithium Batteries and Cathode Materials, *Chemical Reviews* **104** (2004) 4271-4301. <https://doi.org/10.1021/Cr020731c>
- [4] X.-B. Cheng, R. Zhang, C.-Z. Zhao, Q. Zhang, Toward Safe Lithium Metal Anode in Rechargeable Batteries: A Review, *Chemical Reviews* **117** (2017) 10403-10473. <https://doi.org/10.1021/acs.chemrev.7b00115>
- [5] X. Zhang, Y. Yang, Z. Zhou, Towards practical lithium-metal anodes, *Chemical Society Reviews* **49** (2020) 3040-3071. <https://doi.org/10.1039/C9CS00838A>

- [6] Q. Liu, C. Du, B. Shen, P. Zuo, X. Cheng, Y. Ma, G. Yin, Y. Gao, Understanding Undesirable Anode Lithium Plating Issues in Lithium-Ion Batteries, *RSC Advances* **6** (2016) 88683-88700. <https://doi.org/10.1039/C6RA19482F>
- [7] L. Frenck, G.K. Sethi, J. A. Maslyn, N. P. Balsara, Factors That Control the Formation of Dendrites and Other Morphologies on Lithium Metal Anodes, *Frontiers in Energy Research* **7** (2019) 115. <https://doi.org/10.3389/fenrg.2019.00115>
- [8] T. Waldmann, B.-I. Hogg, M. Wohlfahrt-Mehrens, Li Plating as Unwanted Side Reaction in Commercial Li-Ion Cells, *Journal of Power Sources* **384** (2018) 107-124. <https://doi.org/10.1016/j.jpowsour.2018.02.063>.
- [9] D. Cao, X. Sun, Q. Li, A. Natan, P. Xiang, H. Zhu, Lithium Dendrite in All-Solid-State Batteries: Growth Mechanisms, Suppression Strategies, and Characterizations, *Matter* **3** (2020) 57-94. <https://doi.org/10.1016/j.matt.2020.03.015>
- [10] A. J. Louli, A. Eldesoky, R. Weber, M. Genovese, M. Coon, J. deGooyer, Z. Deng, R. T. White, J. Lee, T. Rodgers, R. Petibon, S. Hy, S. J. H. Cheng, J. R. Dahn, Diagnosing and correcting anode-free cell failure via electrolyte and morphological analysis, *Nature Energy* **5** (2020) 693-702. <https://doi.org/10.1038/s41560-020-0668-8>
- [11] G. Homann, L. Stolz, K. Neuhaus, M. Winter, J. Kasnatscheew, Effective Optimization of High Voltage Solid-State Lithium Batteries by Using Poly(ethylene oxide)-Based Polymer Electrolyte with Semi-Interpenetrating Network, *Advanced Functional Materials* **30(46)** (2020) 2006289. <https://doi.org/10.1002/adfm.202006289>
- [12] G. Homann, L. Stolz, M. Winter, J. Kasnatscheew, Elimination of “Voltage Noise” of Poly (Ethylene Oxide)-Based Solid Electrolytes in High-Voltage Lithium Batteries: Linear versus Network Polymers, *iScience* **23** (2020) 101225. <https://doi.org/10.1016/j.isci.2020.101225>
- [13] G. Homann, L. Stolz, J. Nair, I.C. Laskovic, M. Winter, J. Kasnatscheew, Poly(Ethylene Oxide)-based Electrolyte for Solid-State-Lithium-Batteries with High Voltage Positive Electrodes: Evaluating the Role of Electrolyte Oxidation in Rapid Cell Failure, *Scientific Reports* **10** (2020) 4390. <https://doi.org/10.1038/s41598-020-61373-9>
- [14] L. Stolz, G. Homann, M. Winter, J. Kasnatscheew, Realizing poly(ethylene oxide) as a polymer for solid electrolytes in high voltage lithium batteries via simple modification of the cell setup, *Materials Advances* **2** (2021) 3251-3256. <https://doi.org/10.1039/d1ma00009h>.
- [15] S. Klein, P. Barmann, O. Fromm, K. Borzutzki, J. Reiter, Q. Fan, M. Winter, T. Placke, J. Kasnatscheew, Prospects and limitations of single-crystal cathode materials to overcome cross-talk phenomena in high-voltage lithium ion cells, *Journal of Materials Chemistry A* **9** (2021) 7546. <https://doi.org/10.1039/d0ta11775g>.
- [16] S. Klein, P. Harte, S. van Wickeren, K. Borzutzki, S. Roser, P. Barmann, S. Nowak, M. Winter, T. Placke, J. Kasnatscheew, Re-evaluating common electrolyte additives for high-voltage lithium ion batteries, *Cell Reports Physical Science* **2** (2021) 100521. <https://doi.org/10.1016/j.xcrp.2021.100521>
- [17] S. Klein, S. van Wickeren, S. Röser, P. Barmann, K. Borzutzki, B. Heidrich, M. Börner, M. Winter, T. Placke, J. Kasnatscheew, Understanding the Outstanding High-Voltage Performance of NCM523 | Graphite Lithium Ion Cells after Elimination of Ethylene Carbonate Solvent from Conventional Electrolyte, *Advanced Energy Materials* **11** (2021) 2003738. <https://doi.org/10.1002/aenm.202003738>
- [18] S. Klein, J. M. Wrogemann, S. van Wickeren, P. Harte, P. Barmann, B. Heidrich, J. Hesper, K. Borzutzki, S. Nowak, M. Borner, M. Winter, J. Kasnatscheew, T. Placke, Understanding the Role of Commercial Separators and Their Reactivity toward LiPF₆ on the Failure Mechanism of High-Voltage NCM523 | Graphite Lithium Ion Cells, *Advanced Energy Materials* **12** (2022) 2102599. <https://doi.org/10.1002/aenm.202102599>

- [19] K. Kanamura, S. Shiraishi, Z. Takehara, Electrochemical deposition of very smooth lithium using nonaqueous electrolytes containing HF, *Journal of The Electrochemical Society* **143** (1996) 2187-2197. <https://doi.org/10.1149/1.1836979>
- [20] T. Matsui, K. Takeyama, Lithium deposit morphology from polymer electrolytes, *Electrochimica Acta* **40** (1995) 2165-2169. [https://doi.org/10.1016/0013-4686\(95\)00158-B](https://doi.org/10.1016/0013-4686(95)00158-B)
- [21] S. Choudhury, The Many Shapes of Lithium, *Joule* **2** (2018) 2201-2203. <https://doi.org/10.1016/j.joule.2018.11.001>
- [22] D. Aurbach, Y. Gofer, M. Benzion, P. Aped, The behavior of lithium electrodes in propylene and ethylene carbonate - the major factors that influence li cycling efficiency, *Journal of Electroanalytical Chemistry* **339** (1992) 451-471. [https://doi.org/10.1016/0022-0728\(92\)80467-i](https://doi.org/10.1016/0022-0728(92)80467-i).
- [23] D. Aurbach, E. Zinigrad, Y. Cohen, H. Teller, A short review of failure mechanisms of lithium metal and lithiated graphite anodes in liquid electrolyte solutions, *Solid State Ionics* **148** (2002) 405-416. [https://doi.org/10.1016/S0167-2738\(02\)00080-2](https://doi.org/10.1016/S0167-2738(02)00080-2)
- [24] P. Bai, J. Guo, M. Wang, A. Kushima, L. Su, J. Li, F. R. Brushett, M. Z. Bazant, Interactions between Lithium Growths and Nanoporous Ceramic Separators, *Joule* **2** (2018) 2434-2449. <https://doi.org/10.1016/j.joule.2018.08.018>
- [25] J.-H. Han, E. Khoo, P. Bai, M.Z. Bazant, Over-limiting Current and Control of Dendritic Growth by Surface Conduction in Nanopores, *Scientific Reports* **4** (2014) 7056. <https://doi.org/10.1038/srep07056>
- [26] P. Bai, J. Li, F. R. Brushett, M. Z. Bazant, Transition of lithium growth mechanisms in liquid electrolytes, *Energy & Environmental Science* **9** (2016) 3221-3229. <https://doi.org/10.1039/C6EE01674J>
- [27] D. Deng, E. V. Dydek, J.-H. Han, S. Schlumpberger, A. Mani, B. Zaltzman, M. Z. Bazant, Overlimiting Current and Shock Electrodialysis in Porous Media, *Langmuir* **29** (2013) 16167-16177. <https://doi.org/10.1021/la4040547>
- [28] J. Mindemark, M. J. Lacey, T. Bowden, D. Brandell, Beyond PEO-Alternative host materials for Li⁺-conducting solid polymer electrolytes, *Progress in Polymer Science* **81** (2018) 114-143. <https://doi.org/10.1016/j.progpolymsci.2017.12.004>
- [29] Z. G. Xue, D. He, X. L. Xie, Poly(ethylene oxide)-based electrolytes for lithium-ion batteries, *Journal of Materials Chemistry A* **3** (2015) 19218-19253. <https://doi.org/10.1039/c5ta03471j>
- [30] K. N. Jung, H. S. Shin, M. S. Park, J.W. Lee, Solid-State Lithium Batteries: Bipolar Design, Fabrication, and Electrochemistry, *ChemElectroChem* **6** (2019) 3842-3859. <https://doi.org/10.1002/celec.201900736>
- [31] F. B. Dias, L. Plomp, J. B. J. Veldhuis, Trends in Polymer Electrolytes for Secondary Lithium Batteries, *Journal of Power Sources* **88** (2000) 169-191. [https://doi.org/10.1016/s0378-7753\(99\)00529-7](https://doi.org/10.1016/s0378-7753(99)00529-7)
- [32] C. Brissot, M. Rosso, J. N. Chazalviel, S. Lascaud, Dendritic growth mechanisms in lithium/polymer cells, *Journal of Power Sources* **81** (1999) 925-929. [https://doi.org/10.1016/s0378-7753\(98\)00242-0](https://doi.org/10.1016/s0378-7753(98)00242-0)
- [33] L. Stolz, G. Homann, M. Winter, J. Kasnatscheew, Kinetic threshold limits in solid-state lithium batteries: Data on practical relevance of sand equation, *Data in Brief* **34** (2021) 106688. <https://doi.org/10.1016/j.dib.2020.106688>
- [34] L. Stolz, G. Homann, M. Winter, J. Kasnatscheew, The Sand equation and its enormous practical relevance for solid-state lithium metal batteries, *Materials Today* **44** (2021) 9-14. <https://doi.org/10.1016/j.mattod.2020.11.025>
- [35] L. Stolz, G. Homann, M. Winter, J. Kasnatscheew, Area Oversizing of Lithium Metal Electrodes in Solid-State Batteries: Relevance for Overvoltage and thus Performance?, *ChemSusChem* **14** (2021) 2163-2169. <https://doi.org/10.1002/cssc.202100213>

- [36] L. Stolz, S. Roser, G. Homann, M. Winter, J. Kasnatscheew, Pragmatic Approaches to Correlate between the Physicochemical Properties of a Linear Poly(ethylene oxide)-Based Solid Polymer Electrolyte and the Performance in a High-Voltage Li-Metal Battery, *Journal of Physical Chemistry C* **125** (2021) 18089-18097. <https://doi.org/10.1021/acs.jpcc.1c03614>
- [37] L. Stolz, S. Hochstadt, S. Roser, M. R. Hansen, M. Winter, J. Kasnatscheew, Single-Ion versus Dual-Ion Conducting Electrolytes: The Relevance of Concentration Polarization in Solid-State Batteries, *ACS Applied Materials & Interfaces* **14** (2022) 11559-11566. <https://doi.org/10.1021/acsami.2c00084>
- [38] J. Zhang, Y. Zhong, S. Wang, D. Han, M. Xiao, L. Sun, Y. Meng, Artificial Single-Ion Conducting Polymer Solid Electrolyte Interphase Layer toward Highly Stable Lithium Anode, *ACS Applied Energy Materials* **4** (2021) 862-869. <https://doi.org/10.1021/acsaem.0c02740>
- [39] C. Li, B. Qin, Y. Zhang, A. Varzi, S. Passerini, J. Wang, J. Dong, D. Zeng, Z. Liu, H. Cheng, Single-Ion Conducting Electrolyte Based on Electrospun Nanofibers for High-Performance Lithium Batteries, *Advanced Energy Materials* **9** (2019) 1803422. <https://doi.org/10.1002/aenm.201803422>
- [40] L. Xu, S. Tang, Y. Cheng, K. Wang, J. Liang, C. Liu, Y.-C. Cao, F. Wei, L. Mai, Interfaces in Solid-State Lithium Batteries, *Joule* **2** (2018) 1991-2015. <https://doi.org/10.1016/j.joule.2018.07.009>
- [41] J. Gao, C. Wang, D.-W. Han, D.-M. Shin, Single-ion conducting polymer electrolytes as a key jigsaw piece for next-generation battery applications, *Chemical Science* **12** (2021) 13248-13272. <https://doi.org/10.1039/D1SC04023E>
- [42] K. Xu, Nonaqueous Liquid Electrolytes for Lithium-based Rechargeable Batteries, *Chemical Reviews* **104** (2004) 4303-4417. <https://doi.org/10.1021/Cr030203g>
- [43] J. Kasnatscheew, R. Wagner, M. Winter, I. Cekic-Laskovic, Interfaces and Materials in Lithium Ion Batteries: Challenges for Theoretical Electrochemistry, *Topics in Current Chemistry* **376** (2018) 16. <https://doi.org/10.1007/s41061-018-0196-1>
- [44] I. Cekic-Laskovic, N. von Aspern, L. Imholt, S. Kaymaksiz, K. Oldiges, B. R. Rad, M. Winter, Synergistic Effect of Blended Components in Nonaqueous Electrolytes for Lithium Ion Batteries, *Topics in Current Chemistry* **375** (2017) 37. <https://doi.org/10.1007/s41061-017-0125-8>
- [45] L. Stolz, G. Homann, M. Winter, J. Kasnatscheew, Kinetic Threshold Limits in Solid-State Lithium Batteries: Data on Practical Relevance of Sand Equation, *Data in Brief* **34** (2021) 106688. <https://doi.org/10.1016/j.dib.2020.106688>
- [46] P.G. Bruce, C.A. Vincent, Steady-State Current Flow in Solid Binary Electrolyte Cells, *Journal of Electroanalytical Chemistry* **225** (1987) 1-17. [https://doi.org/10.1016/0022-0728\(87\)80001-3](https://doi.org/10.1016/0022-0728(87)80001-3)
- [47] G. Homann, L. Stolz, J. Nair, I.C. Laskovic, M. Winter, J. Kasnatscheew, Poly(Ethylene Oxide)-based Electrolyte for Solid-State-Lithium-Batteries with High Voltage Positive Electrodes: Evaluating the Role of Electrolyte Oxidation in Rapid Cell Failure, *Scientific Reports* **10** (2020) 4390. <https://doi.org/10.1038/s41598-020-61373-9>
- [48] J. Kasnatscheew, B. Streipert, S. Roser, R. Wagner, I.C. Laskovic, M. Winter, Determining oxidative stability of battery electrolytes: validity of common electrochemical stability window (ESW) data and alternative strategies, *Physical Chemistry Chemical Physics* **19** (2017) 16078-16086. <https://doi.org/10.1039/c7cp03072j>
- [49] J.R. Nair, L. Imholt, G. Brunklau, M. Winter, Lithium Metal Polymer Electrolyte Batteries: Opportunities and Challenges, *The Electrochemical Society Interface* **28** (2019) 55-61. <https://doi.org/10.1149/2.F05192if>

- [50] M. Rosso, C. Brissot, A. Teyssot, M. Dollé, L. Sannier, J.-M. Tarascon, R. Bouchet, S. Lascaud, Dendrite short-circuit and fuse effect on Li/polymer/Li cells, *Electrochimica Acta* **51** (2006) 5334-5340. <https://doi.org/10.1016/j.electacta.2006.02.004>